

Topical Review

Shape memory polymers and their composites in aerospace applications: a review

Yanju Liu¹, Haiyang Du¹, Liwu Liu¹ and Jinsong Leng²

¹ Department of Astronautical Science and Mechanics, Harbin Institute of Technology (HIT), PO Box 301, No. 92 West Dazhi Street, Harbin 150001, People's Republic of China

² Centre for Composite Materials, Science Park of Harbin Institute of Technology (HIT), PO Box 3011, No. 2 Yikuang Street, Harbin 150080, People's Republic of China

E-mail: lengjs@hit.edu.cn

Received 5 March 2013, in final form 11 July 2013

Published 9 January 2014

Abstract

As a new class of smart materials, shape memory polymers and their composites (SMPs and SMPCs) can respond to specific external stimulus and remember the original shape. There are many types of stimulus methods to actuate the deformation of SMPs and SMPCs, of which the thermal- and electro-responsive components and structures are common. In this review, the general mechanism of SMPs and SMPCs are first introduced, the stimulus methods are then discussed to demonstrate the shape recovery effect, and finally, the applications of SMPs and SMPCs that are reinforced with fiber materials in aerospace are reviewed. SMPC hinges and booms are discussed in the part on components; the booms can be divided again into foldable SMPC truss booms, coilable SMPC truss booms and storable tubular extendible member (STEM) booms. In terms of SMPC structures, the solar array and deployable panel, reflector antenna and morphing wing are introduced in detail. Considering the factors of weight, recovery force and shock effect, SMPCs are expected to have great potential applications in aerospace.

Keywords: shape memory polymer (SMP), shape memory polymer composite (SMPC), aerospace, application

(Some figures may appear in colour only in the online journal)

Contents

1. Introduction	1	4.2. SMPC components in aerospace	5
2. General mechanism of SMPs and SMPCs	2	4.3. Structures based on SMPC components in aerospace	8
3. Stimulus methods of SMPs and SMPCs	3	5. Conclusions	16
3.1. Thermal-responsive SMPs and SMPCs	3	Acknowledgments	16
3.2. Electro-responsive SMPs and SMPCs	4	References	17
3.3. Other stimulus methods of SMPs and SMPCs	4	1. Introduction	
4. Applications of SMPCs in aerospace	4	Shape memory polymer (SMP) is a type of macromolecular smart material that can respond to external stimulus by	
4.1. Space environment evaluation and related testing	4		

changing its macroscopic properties (such as shape and color) and then recover its original shape from its temporary shape [1–10]. Additionally, SMPs have the unique advantages of being lightweight and inexpensive and of having low density, good manufacturability, high shape deformability, good biodegradability and an easily tailorable glass transition temperature compared with shape memory alloys (SMAs) and shape memory ceramics [11–20]. Therefore, an increasing number of international researchers have been focusing on the development of the shape memory effect in polymers since the 1980s, particularly in the last few years [2, 8–10]. However, SMPs also have some drawbacks, such as low deformation stiffness and low recovery stress [21–23]. To overcome these deficiencies, shape memory polymer composites (SMPCs) have been developed in practical applications to satisfy demand, the results of studies on SMPCs indicate that SMPCs have higher strength, higher stiffness and certain special characteristics determined by what fillers are added, which can offer further advantages over SMPs [1–10, 21–29]. Meanwhile, some novel functional SMPs (functionally graded SMPs [30], multi-shape SMPs [31–36], two-way SMPs [37–40], self-healing SMP [41–43] and SMP foams [44–47]) have also been developed. Today, SMPs and SMPCs cover applications ranging from outer space to submarines (including aerospace [48–53], biomedicine [54–59], textiles [60–64] and automobiles [65–68]).

There are some excellent reviews about the development and application of SMPs and SMPCs, such as a review written by Wei *et al* on the research and development of shape memory materials (SMA, shape memory ceramics, SMP and SMPC) up to 1998, in which the properties of stimulus-induced phase transition of SMP are discussed in detail [13]; another excellent review written by Lendlein *et al* shows the multifunctionality of SMP and SMPC except shape memory effect based on different polymer network cross-linked structures, such as the properties of permeability, transparency and conductivity, and so on [2]. In addition, Leng *et al* give a summary of the fabrication, characterization, models, stimulus methods and application fields of SMP and SMPC, in which the stimulus methods and application fields are discussed in detail [8]; Xie has reviewed the recent development of SMP up to 2011, in which the main content is focused on all kinds of shape memory phenomena, such as conventional dual-shape SMP, triple-shape SMP, tunable multi-shape SMP, two-way SMP, and so on [34]; Hu *et al* give an extensive review of the concept, synthesis methods, stimulus methods, analysis models and applications (especially in textiles) of SMP and SMPC [10]. All of the above-mentioned reviews focus on some special interests or give an extensive summary. In this review, the applications of SMPs and SMPCs in the aerospace field are discussed in detail, including SMPC hinges, truss booms, reflector antennas, morphing structures, lunar habitats and mandrel fabrication. There is no doubt that SMPs and SMPCs will play an increasingly important role in aerospace in the future.

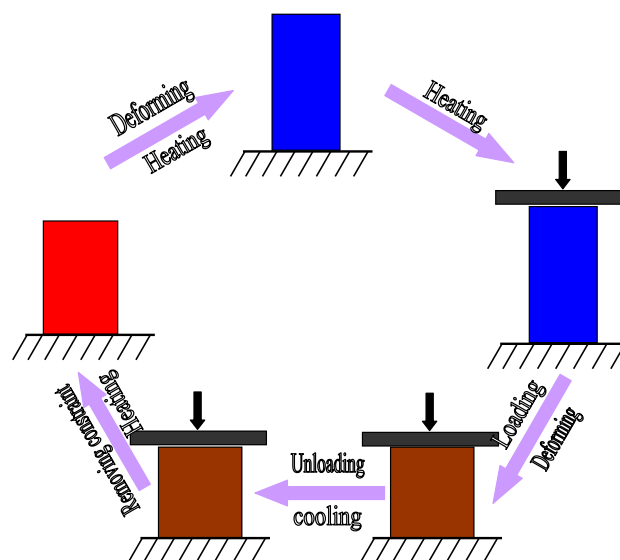


Figure 1. The typical thermomechanical cycle processing of a SMP/SMPC under compression testing.

2. General mechanism of SMPs and SMPCs

The main characteristics of SMPs and SMPCs are their variable material properties above and below the transition temperature (glass transition temperature (T_g) or melting transition temperature (T_m) based on the nature of the polymer configuration). Taking T_g for example, when the temperature is higher than T_g , the polymer is in the rubber state and is considered a viscous material; however, when the temperature is below T_g , the polymer is in the glass state and is considered an elastic material. Near the transition temperature, SMPs exhibit viscoelastic behavior, in which the polymer properties change rapidly and the elasticity modulus decreases by approximately two orders of magnitude [69–71]. In general, SMPs and SMPCs are commonly used in deployable structures. There are typical thermomechanical cycles of SMP or SMPC in the process of shape memory and recovery, as demonstrated in figure 1. The shape recovery process consists of the following steps. (1) Original step, fabricating the original shape of the SMP. (2) Heating step (above T_g), deforming the SMP to a pre-deformed shape. (3) Cooling step, reducing the temperature to a low temperature (below T_g) and removing the constraint. (4) Reheating step, increasing the temperature to the high-temperature state and recovering the original shape [1–10].

Based on the different molecular cross-linked architectures, SMPs/SMPCs can be classified into two types: thermoplastic and thermoset [2, 8, 72]. In the past few decades, research has mainly focused on thermoplastic SMPs/SMPCs, such as shape memory polyurethane (SMPU). Unfortunately, the components and structures made by thermoplastic SMPs lose their shape memory effect after several cycles. Therefore, thermoset SMPs/SMPCs with high material stiffness, high transition temperature and environmental durability are becoming the potential selection for the fabrication of space structures. In table 1, partial

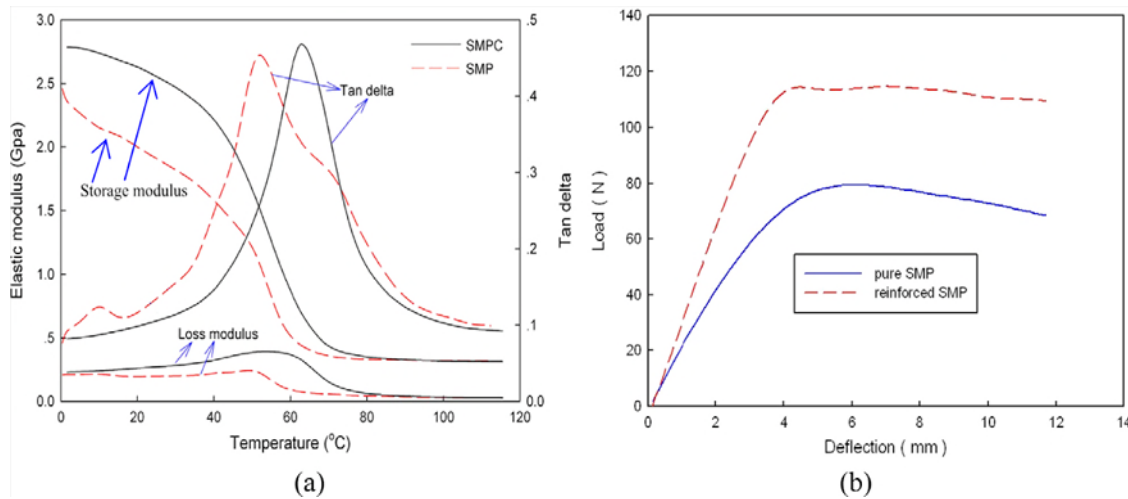


Figure 2. DMA testing of styrene-based SMPC. from [25]. Copyright ©2009, World Scientific.

Table 1. Partial list of currently available thermoset SMP matrix materials with broad tunable transition temperature.

Designers	Thermoset SMP matrix materials	Glass transition/deformation temperature (°C)
Xie and Rousseau [73]	Epoxy	30–89
Rousseau and Xie [74]	Epoxy	44–93
Leng <i>et al</i> [75]	Epoxy	37–96
Li and Larock [76]	Polystyrene	52–69
Zhang <i>et al</i> [77]	Polystyrene	63–74
Shumaker <i>et al</i> [78]	Polyaspartimide–urea	110–164
Biju <i>et al</i> [79]	Cyanate–ester–epoxy–poly(tetramethyleneoxide)	72/94
Xie <i>et al</i> [80]	Cyanate–ester	156.9–256.9
CTD [81]	CTD-400 cyanate–ester series	159–238
CRG [82]	Polystyrene	45–106
ILC [83]	TP series	53–108

research reported with broad tunable range of T_g is listed to show the thermomechanical behavior of different cross-linked structural thermoset SMPs and SMPCs.

To date, many research works have been carried out to investigate the thermomechanical behavior of SMPs and SMPCs, with various testing results (such as from uniaxial tensile, compression and three-point flexure tests); researchers explain the shape memory phenomenon and theory using two main approaches [84, 85]. One approach is based on viscoelastic theory. In the early years, Tobushi *et al* [86–88] investigated the thermomechanical behavior of SMPU using this theory. In this model, the materials are assumed to be a combination of three types of basic elements: a spring, which represents elasticity properties, a dashpot, which represents viscous properties, and a frictional element, which represents the slip mechanism due to internal friction. Their collaboration in series or in parallel can be used to represent viscoelastic properties of SMPU. The other approach is based on phase transition (frozen phase and active phase) theory. Liu *et al* [89, 90] developed a small strain and rate-independent thermomechanical constitutive model of epoxy SMP using this theory. In this model, the internal variables are defined and the materials are commonly considered to own the state of active phase and frozen phase.

Moreover, SMPCs are considered to be a combination of the matrix materials (SMP) and the reinforcing materials; the reinforcing materials (such as carbon black, carbon nanotubes, short fibers and continuous fibers), which constitute some volume fraction of the matrices, are considered to have good compatibility with the matrices and strengthen the thermal, mechanical and other properties. As shown in figure 2, the glass transition temperature and storage modulus of styrene-based fiber-reinforced SMP are significantly higher than for pure SMP by dynamic mechanical analysis (DMA) [25].

3. Stimulus methods of SMPs and SMPCs

SMPs and SMPCs exhibit the shape memory effect as a result of various stimuli and polymer matrices [91–95]. For stimulus methods, heat-induced and electricity-induced SMPs and SMPCs are most typical. Additionally, light, magnetic field, water and solvent can also actuate the shape memory recovery of SMP and SMPC components and structures.

3.1. Thermal-responsive SMPs and SMPCs

Thermal-responsive SMPs and SMPCs are the earliest and most common type. Much research has focused on the

thermomechanical behavior and applications of thermal-responsive SMPs and SMPCs [86–88, 96–100].

Tobushi *et al* investigated the thermomechanical behavior of SMPU with a small and large strain by tensile test and validated the good shape fixity ratio and shape recovery ratio of SMPU [86–88]. The free and constrained recovery of SMP also was investigated by Qi *et al*: a three-dimensional finite deformation constitutive model was used to simulate the loading/deformation process of compression test [96, 97]. Additionally, Gall *et al* compared the thermomechanical behavior of pure epoxy SMP resin with SMPC reinforced with nano-scale SiC by the three-point flexure test; the results showed that the SMPC owned higher elastic modulus and recovery force [98]. Moreover, Leng *et al* compared the deployment process of pure SMP with glass-fiber-reinforced SMP to validate the shape memory effect of SMPs and SMPCs [8]. In addition, Leng *et al* verify that SMPCs also exhibit certain functions due to the intrinsic properties of the filler, such as that the mechanical properties of SMPC reinforced with carbon particles are improved in addition to the change in electrical conductivity, except undergoing the shape memory effect similar to SMPs [8, 9].

The above-mentioned deploying process of thermal-responsive SMPs and SMPCs only occurs in a one-dimensional (1D) direction, and the process is relatively simple. Currently, SMPs and SMPCs can be used to simulate the deploying or packaging of relatively complex structures, such as solar arrays or morphing wing structure models, when the raw materials are selected effectively [2].

3.2. Electro-responsive SMPs and SMPCs

The electro-responsive SMPC is another type of common structures, in which electrically conductive fillers are incorporated into the SMP matrices to form electrically sensitive structures [101, 102]. Goo *et al* studied the shape recovery process of SMPU reinforced with multi-walled carbon nanotubes (MWNTs) to improve the mechanical properties and electrical conductivity [103, 104]. Hu *et al* fabricated SMPU composites reinforced with MWNTs to demonstrate the good shape recovery effect with different reinforcing phase volume fraction and the shape recovery stress trend under different thermomechanical cycles [105, 106]. Additionally, carbon nanopaper was selected as a new reinforcing material to investigate the electrical conductivity change of SMPs and SMPCs by Lv *et al* [107, 108].

Leng *et al* analyzed the change trends of electrical conductivity and electrical resistivity of a SMP reinforced with nanocarbon powders or fibers [109–115]. The SMPU experiment results showed that the micro-sized Ni powder formed chains under a weak external magnetic field, which can strengthen significantly the electrical conductivity in the chain direction [111]. Moreover, when a small amount of Ni powders was added to the SMP filled with carbon black, the electrical resistivity can reduce significantly when the Ni powders form chains; otherwise, the effect is slight [112]. Further, the electrical and thermomechanical properties of a SMPC filled with hybrid fibers were investigated by

Leng *et al* [113–115]. Considering the relationship between strain and electrical resistivity with different temperature, electro-responsive SMPs can be fabricated to be smart strain structures or temperature sensors in application [116, 117].

3.3. Other stimulus methods of SMPs and SMPCs

In addition to the above-mentioned stimulus methods, light radiation, change of magnetic field and water/solvent will also play a role in future applications.

Light-responsive SMPs and SMPCs can be classified into two types: the intrinsically light-induced SMP, which is only sensitive to certain wavelengths of light and is independent of the temperature effect, and the indirect thermal actuation SMPC, which can effectively absorb infrared light and heat to actuate the structure to recover its original shape [2, 8]. The shape memory and recovery process of light-responsive SMPs and SMPCs has been investigated by Lendlein *et al* [118–120], Leng *et al* [121, 122] and Maitland *et al* [123–125].

Magnetic-responsive SMPCs are primarily composed of SMP matrices and magnetic fillers, such as Fe_2O_3 , Fe_3O_4 and Ni particles; the shape memory effect can be actuated using an alternating external magnetic field [126–131].

Water/solvents can be used as plasticizers to reduce the glass transition temperature and trigger the shape recovery process at relatively low temperature compared to the original SMP/SMPCs [8]. Huang *et al* [132–134] and Lv *et al* [135, 136] investigated the plasticizing effect of water/solvents on polymer deformation.

4. Applications of SMPCs in aerospace

4.1. Space environment evaluation and related testing

Nowadays, much research is devoted to the SMP/SMPC applications in aerospace. However, space environment is extremely harsh, and many important factors must be considered when selecting structure materials in space environment, such as high vacuum, ultra-high or low temperature cycle effect, ultraviolet (UV) radiation, and so on; they can decrease the work effectiveness of solar arrays and increase the challenge component to normal work [137–139]. Some necessary testing must be done before application of SMPs and SMPCs in space-deployable structures. Fukher *et al* studied the influence of radialization on thermoset styrene SMP, in which the nanoindentation testing has been carried out to show the mechanical properties after radialization [140]. Leng *et al* investigated the influence of γ -radiation on the structures properties of epoxy SMPs by the DMA test and tensile test [141]. The results showed that the value of tensile strength reduced significantly after higher γ -radiation dosage, as shown in figure 3. Moreover, considering the ultra-high or low temperature of space environment, the thermoset shape memory cyanate polymer (SMCP) with a unique high glass transition temperature is investigated and discussed in relation to use in aerospace [142].

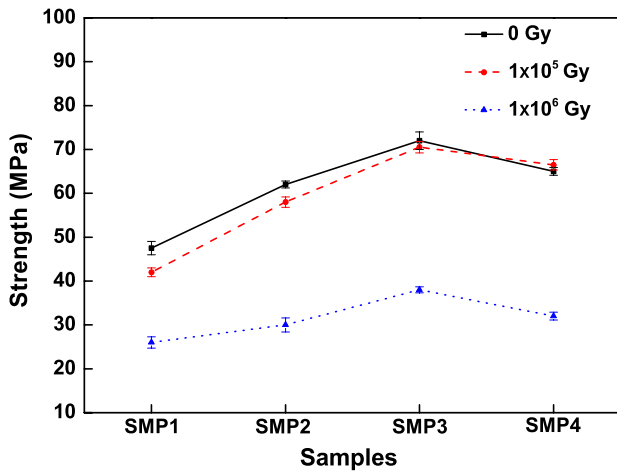


Figure 3. Tensile strength of epoxy-based SMPs before and after γ -irradiation [141]. Copyright 2013, Sage.

4.2. SMPC components in aerospace

In this section, several space-deployable components are introduced in detail, and a brief review concerning their development history and current application state are provided. Due to the traditional structures having some intrinsic disadvantages, such as high weight, high cost and high deployable shock effect, which will take up much room in spacecraft and decrease the effectiveness of aerospace missions, some new kinds of materials and structures have been developed to improve the effective space usage in the device. On the other hand, SMP/SMPC, which can be packaged and deployed with simple mechanical properties under a variety of external environments, is attracting more and more attention. Based on all the advantages of SMP/SMPC mentioned in section 4.1, there is no doubt that SMP/SMPC will be one of the best candidate materials for future aerospace engineering.

4.2.1. SMPC hinges. A hinge can usually be used as the driving device in the deployment process of space-deployable structures; there are many important factors to assess its effectiveness (such as shock effect and recovery precision). Traditionally, deployment has depended on a mechanical hinge or tape spring hinge [143]. However, the complex integrated systems of mechanical hinge and large shock effect of spring steel hinge increase the challenge of successful deployment and hinder their development in aerospace [144, 145]. To overcome this issue, Composite Technology Development Inc. (CTD) proposed a new type of hinge composed of elastic memory composite (EMC) materials to reduce the moving parts and shock effect, and results indicated that the novel hinge could provide good controlled deployment ability [146, 147].

The tape spring hinge is one kind of stored strain energy hinge, in which the tape spring can be metal, plastic or composite. The first use of the tape spring hinge dates back to the 1960s. Vyvyan *et al* conceived the self-actuating, self-locking tape spring and introduced the



Figure 4. The early SMPC hinge prototype. Reused from [154] with permission from the authors.

general geometrical configuration in 1968 [148]; Schwartz *et al* conceived a flexible tape spring hinge to hinder the shock effect, in which rubber material can be applied to the metal tape spring to improve the stored strain energy and bending characteristics [149]. In addition, Chiappetta *et al* conceived a tape spring hinge in which the metal tape spring was replaced by composite materials with two tape springs in the equal sense [150]. Besides the experimental research, theory analysis has also attracted attention. Pellegrino *et al* assumed the tape spring as a curved shell spring in some methods and analyzed the tape spring mechanical properties in the equal sense and opposite sense under moments [151–153]. The early EMC hinge prototype is an improvement on the design of tape spring hinges, replacing the tape spring by EMC material to reduce impact during space structural deployment. Although the early EMC hinge design can meet some real project requirements, it is only a preliminary design, and there is much room for improvement, such as in the shape of the EMC tapes and the two end fixture devices.

The early EMC hinge prototype is similar to the hinge invented by Chiappetta *et al* in which the two EMC tapes are in parallel, as shown in figure 4. The experiment results show that when the two EMC tapes have a relatively long distance between each other, a high strain region will be present near the end fixture. This phenomenon will lead to local buckling and damage of the hinge after several cycles; when the distance is too short, the structural stiffness will significantly decrease [154]. To solve this drawback, the geometrical configuration of the prototype can be changed. Based on the equal stiffness rule in the lateral and longitudinal direction of hinge, the tapes in the opposite sense configuration with a half-angle of 120° would be most optimal. However, a half-angle of 90° is usually suitable for design for convenient manufacture; in terms of the design of the end fixture, considering the local buckling and strain distribution rule, parabolic footprint geometry would be ideal to replace rectangle and circle end fixture design [154]. Today, SMPC hinges are increasingly applied in space-deployable structures, and there are several different types to be selected. In addition to the aforementioned EMC hinges, Leng *et al* have developed a type of SMPC hinge reinforced with carbon fibers (figure 5) [8, 155, 156]. This hinge consists of three parts: (1) two circular curved thin shells in the opposite sense, (2) two end fixture devices, (3) two resistor heaters stuck to the surfaces (surface-bonded resistor heater) of the thin shells in the axial direction to actuate the deformation recovery using electricity. To verify the feasibility of this type of SMPC

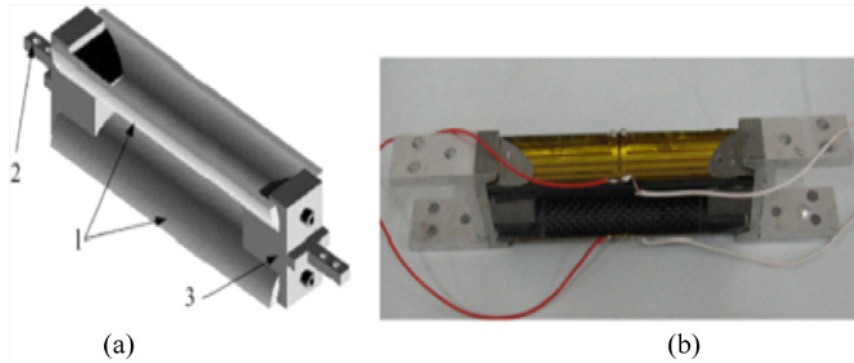


Figure 5. Epoxy-based SMPC hinge reinforced with carbon fiber: (a) illustration prototype of the hinge and (b) real-scale hinge design. Reprinted from [8], Copyright 2011, with permission from Elsevier.

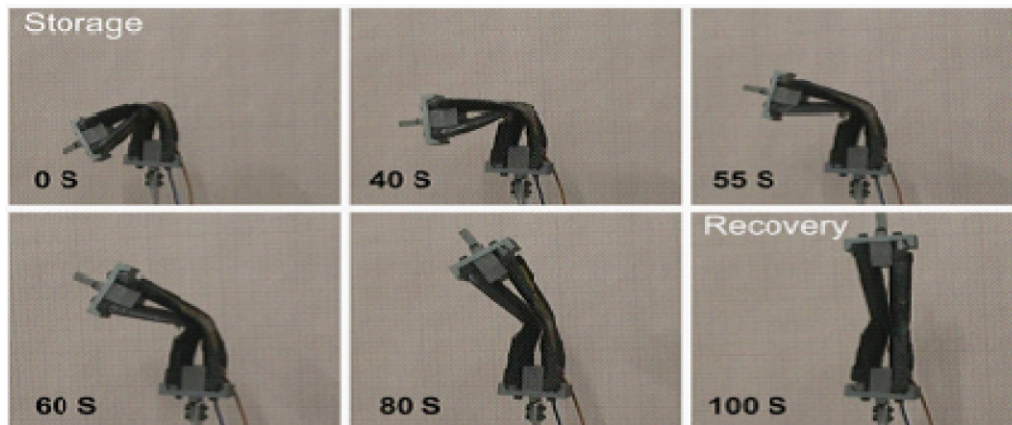


Figure 6. The shape recovery process of SMPC hinge actuated by direct current [156].

hinge, a recovery experiment was performed, in which the bending angle was as high as 140° initially. The recovery process is illustrated in figure 6. The shape recovery ratio is nearly 100%. The velocity varies during the deployment process, with the early stage and final stage being slower than the middle stage, which helps to reduce the shock effect in the deployable structure [156].

4.2.2. SMPC booms. Booms are the main components to support the tip payloads in satellites. Traditionally, the design of a space deployable boom has involved complex assembly and control mechanism and high weight because the materials selected are mostly metals. To overcome this problem, researchers have explored many methods. Today, the existing deployable booms can be divided into two classes: classical traditional booms and novel SMPC booms.

The classical traditional space-deployable booms include tubular, extendible booms and collapsible truss booms actuated by motor. The disadvantages have been listed above [157–161]. In contrast, the novel SMPC not only has simple structure, but also packages and deploys without mechanical devices. Therefore, the unique characteristics of SMPCs have aroused increasing interest for space-deployable structures. The novel types of SMPC booms can be divided into foldable truss booms, coilable truss booms and storable tubular extendible member (STEM) booms. The longeron is the main component of the SMPC boom, which provides the

deployable driving force and undergoes the tip payloads at the end of deployment.

(1) *Foldable SMPC truss booms.* CTD has developed a new type of EMC space-deployable boom under the funding of the Air Force Research Laboratory (APRL) for the United States Air Force Academy (USAFA) FalconSat-3 mission [162, 163]. Two types of boom configurations have been selected as possible best candidate structures. One is a two-longeron truss boom, which will form a tubular-shaped boom after deployment, and the other is a three-longeron truss boom, which will be extensible to a space triangle-shaped truss boom. The prototype is shown in figure 7 [162].

Starsys Research Corporation (SRC) verified the feasibility of EMC truss booms and selected the best structures. The results indicated that each model has some drawbacks during the deployment process. The moving of the two-longeron truss boom and the fastening of the three-longeron truss boom are potential failure factors to successful deployment: finally, the low-moving-part design and light weight of the two-longeron truss boom led to its selection as the preliminary baseline model for the FalconSat-3 mission [162, 163]. However, the structure must be improved to eliminate the drawbacks before implementing this design. After a series of designs, fabrications, measurements and evaluations, the SMPC boom of FalconSat-3 mission was developed, as shown in figure 8. The final truss boom included three semi-cylindrical EMC longerons packaged into a ‘z shape’ for

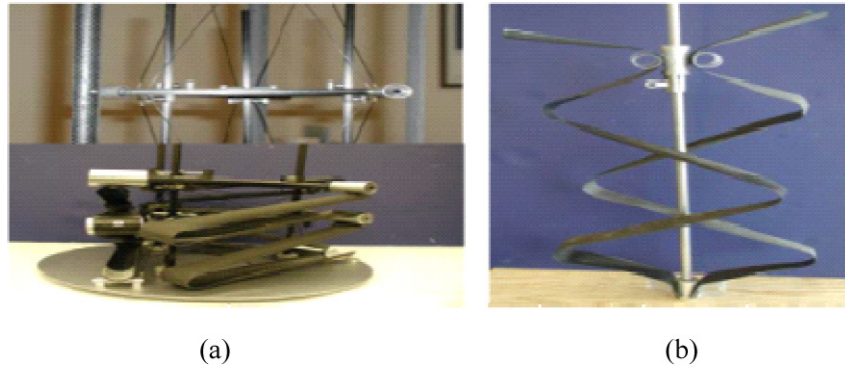


Figure 7. The preliminary SMPC booms design of FalconSat-3 mission: (a) three-longeron truss boom and (b) two-longeron truss boom. Reused from [162] with permission from the authors.

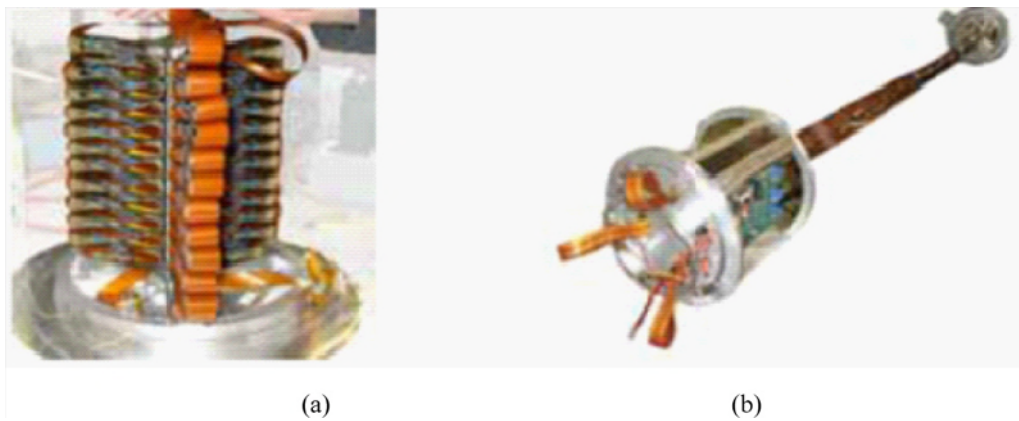


Figure 8. The proposed FalconSat-3 three-longeron EMC tubular boom: (a) the packaged configuration and (b) the deployed configuration. Reused from [144] with permission from the authors.

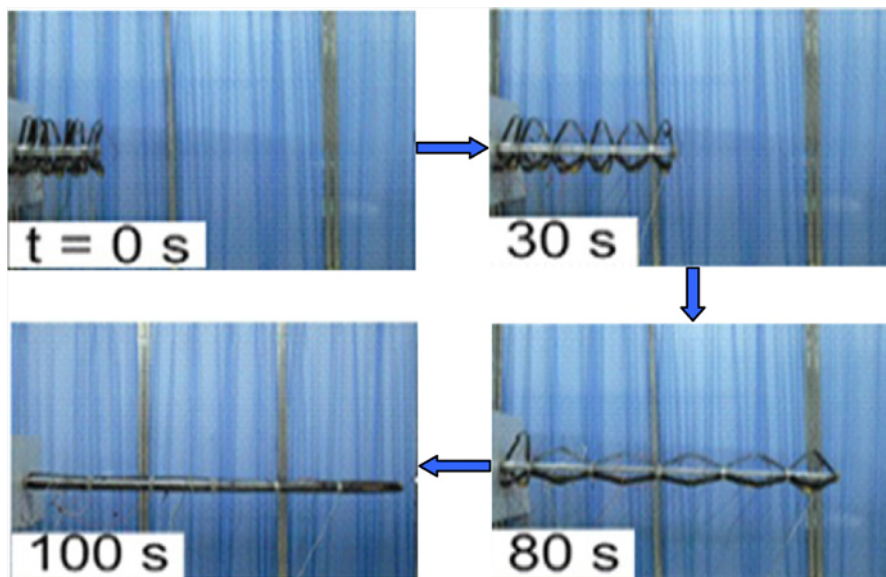


Figure 9. The deployment process of epoxy-based SMPC truss boom.

launch in the vehicle, and a series of resistor heaters embedded into the EMC longeron to actuate deployment in orbit [144].

Recently, Leng *et al* developed a novel type of SMPC truss boom, which consists of 18 pieces of laminate tapes with a semi-cylindrical section in the equal sense, one extendable central bracket, which includes six levels of short hollow rods

that assume good contact area without friction with each short rod containing three laminate tapes with an angle of 120° to each other, and a resistor heater stuck to the concave surface centerline along the axial direction of every laminate tape. The boom is packaged into a 'M-shape' before the experimental evaluation; when performing the experiment, the boom will

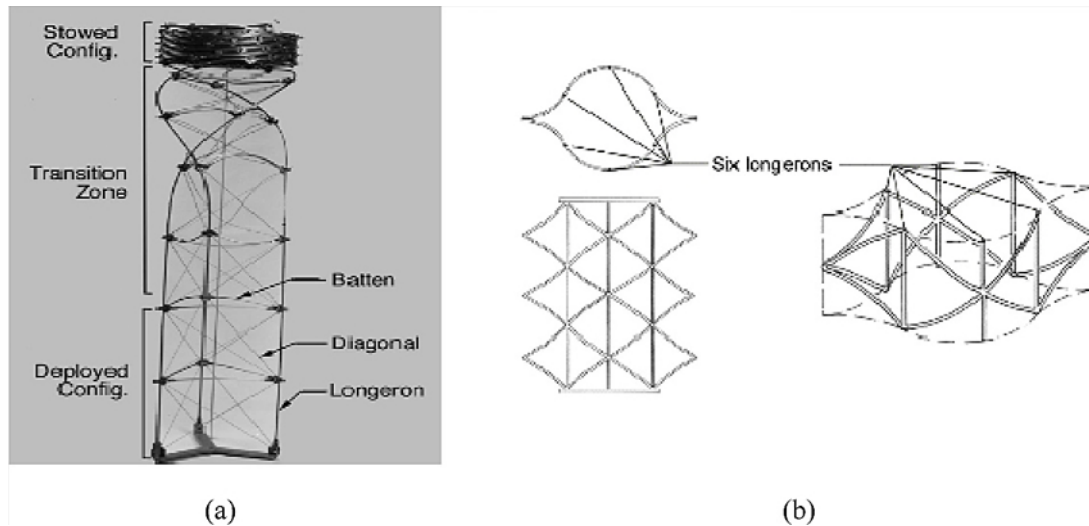


Figure 10. Coilable truss boom, (a) three-longeron boom and (b) six-longeron boom. Reused from [164] with permission from the authors.

gradually deploy with increasing time. The recovery process is presented in figure 9. The structure is very different from the CTD production. First, the sections are in the equal sense, which is related to the deployable recovery force, and second, the structure is divided into some small parts.

(2) *Coilable SMPC truss booms.* The coilable truss boom is another advanced deployable boom, which consists of simple structure and low weight in some respects, simultaneously. However, high strain energy and large relaxation phenomena exist in the stowed state. Nowadays, there are two types of configurations: three-longeron and six-longeron coilable truss booms (figure 10) [164]. The longeron of the boom can be bent or stowed in a small volume and provide stiffness and strength after deployment [164, 165]. The methods of deployment mainly consist of free deployment, cable deployment and tubular deployment.

The three-longeron coilable truss boom is a free-deployment boom, which is typically composed of longeron, lateral batten and diagonal members. S2-glass/epoxy is the main material to fabricate the longeron due to the deformation and mechanical properties. However, the boom will store lots of strain energy and be a safety challenge, when packaged by twisting the boom into a helical or snake shape for launch [164]. To overcome the drawback of high strain energy, the fiber-reinforced composite concept was considered to fabricate the longeron; the results indicated that the EMC longerons can significantly reduce the weight of the boom and the packaged strain energy while simultaneously maintaining the high strain capability [164–166]. There is no doubt that the boom will have a promising future in improving the performance of all types of packaged structures.

(3) *SMPC STEM booms.* The SMPC STEM boom is the other kind of advanced boom extant since the early stages of space exploration, and is of lower weight, higher packaging strain and stronger specific modulus than the traditional STEM boom. Additionally, the SMPC STEM boom has a simpler structure and larger cross-section compared with conventional SMPC booms. To date, some prototype booms

have been fabricated by using STEM technology. In this section, the deployment and packaging technology for a seven meters horizontal SMPC STEM boom (figure 11) will be introduced, and some important factors of the system will be considered [167, 168], such as fabrication technology, assembly technology and deployment-control technology. As to the material fabrication technology, the modification of SMPC component ratio and the curing methods are sensitive to the shape memory effect of the structure. In addition, the final space-deployable boom is usually composed of some small member sections; lap joints are a key part to assemble these sections. Moreover, a deployment control system is imperative for deployment of the structure, which essentially consists of support structure, heater, driving motor and computer controller [168].

Due to SMPC hinges/booms needing to undergo flexural deformation and have minimal strain, the bending mechanical properties and deployment dynamics must be considered in aerospace application [169]. CTD Co. has reported the microbuckling response of reinforced EMC laminates. The results show that the fiber microbuckling can undergo higher flexural deformation without damage at high temperature and store the deformation state at low temperature. When the EMC material is reheated, the microbuckling gradually disappears and the original shape is gradually recovered [170, 171]. Lan *et al* have also investigated the post-microbuckling mechanics of fiber-reinforced SMPC undergoing flexural deformation by considering the material deformation and mechanical properties (figure 12) [172].

4.3. Structures based on SMPC components in aerospace

4.3.1. Solar arrays and deployable panels. Solar arrays are the main energy generation subsystems in space-deployable structures to obtain energy in space and are commonly packaged in the vehicle before launch; once in-orbit, the solar array is released to deploy and collect energy, and its work efficiency is dependent on a large deployment area, reliable

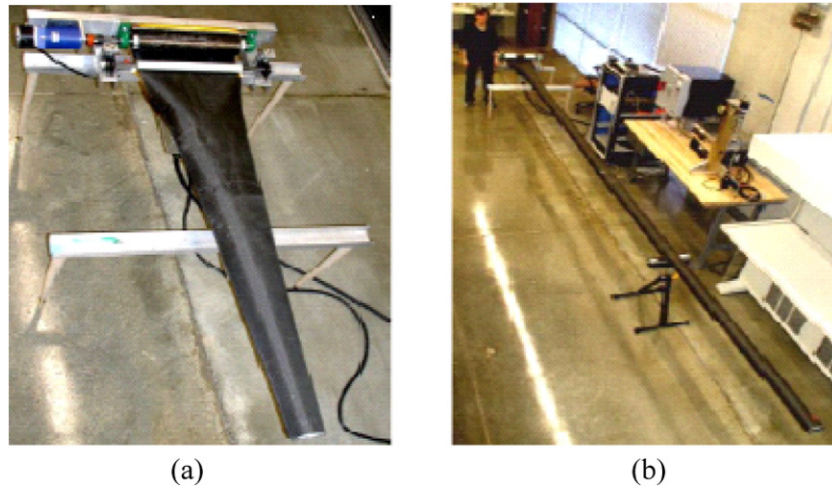


Figure 11. EMC STEM deployed system: (a) partial deploying state and (b) the deployed state. Reused from [168] with permission from the authors.

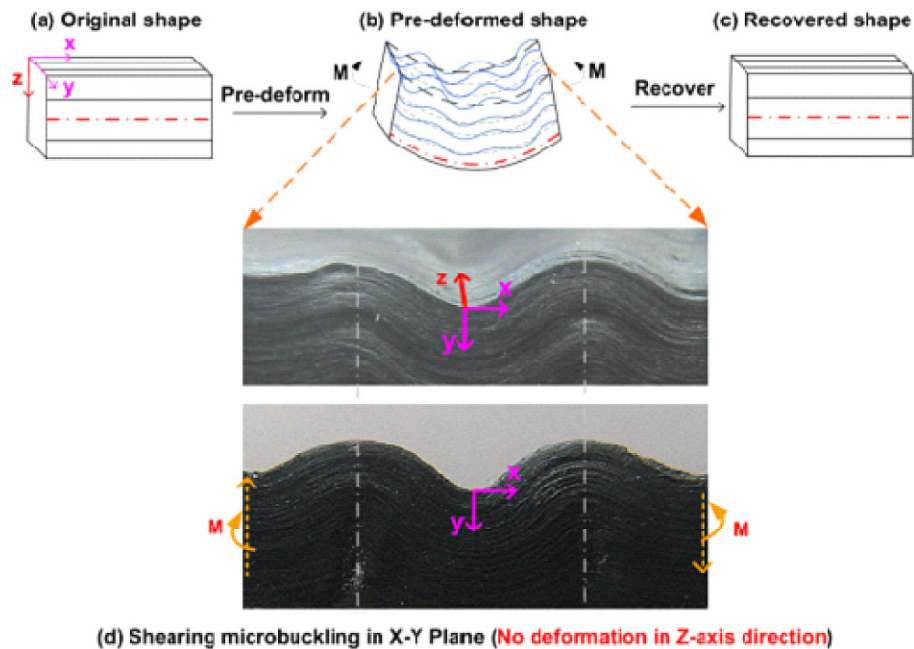


Figure 12. Shearing microbuckling deformation of SMPC laminate. Reused from [172], Copyright 2013, with permission from Elsevier.

stiffness and lightness of weight. Today, solar array structures have different forms, such as rigid, semi-rigid and flexible types [173–179].

Lan *et al* have developed a type of carbon-fiber-reinforced SMPC hinge to actuate solar array deployment and performed an experiment to simulate the deployment process in a zero-gravity environment [156]. The solar array is heated above transition temperature and bent to a pre-deformed angle under an external force, then maintains the force and is allowed to cool to room temperature; after that the prototype is reheated to the same temperature at the same voltage and recovers its original position in 80 s. The deployment process is illustrated in figure 13.

The feasibility of the deployable technology of advanced SMPC solar arrays has been verified by the experiment of

the RoadRunner satellite (250 kg) [144], in which two solar arrays located at the two ends of the satellite are selected as experimental components (figure 14). The configuration of the two solar arrays is the same; however, the hinge materials are different from each other, with one being an EMC hinge and the other being a conventional steel tape-spring hinge [174]. A series of experiments, including a gravity-off load deployment test and a random vibration test, were performed to validate the feasibility of using an EMC hinge to deploy the solar array without damage. The results indicate that the EMC hinge can replace the traditional metal material on some non-critical deployable parts of satellite to increase the work mission [144, 174].

CTD has also designed a type of solar array with low-moving parts, a simple structure and low cost (figure 15).

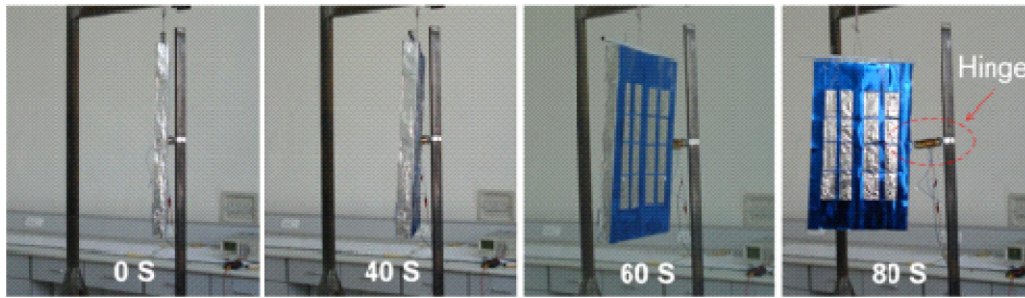


Figure 13. Shape memory process of a solar array prototype actuated by an SMPC hinge [156].

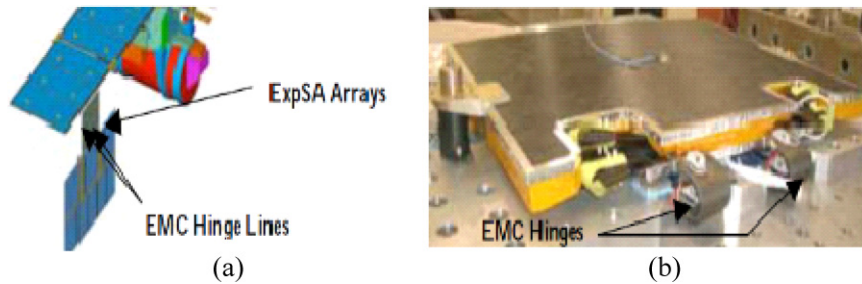


Figure 14. RoadRunner experiment: (a) deployed state and (b) packaged state [144].

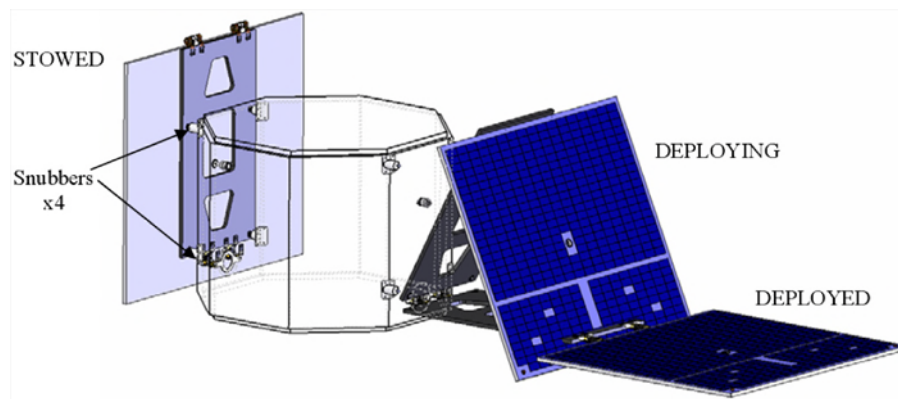


Figure 15. CTD solar array design. Reused from [175] with permission from the authors.

A special mission of the structure is to advance the Operationally Responsive Space (ORS) technology and validate the advantages of the new design to better adapt different types of missions for future small satellites. The key factor of achievement is the use of EMC hinges. The hinge is designed to drive and damp the deployment of the solar array and to lock the shape of array after deployment without driving and locking devices as seen in traditional mechanically deployed arrays [175].

EMC hinges have also been applied to the deployable panels of the Intelligent Nanosat Operations Satellite (DINO Sat) fabricated by a cooperative effort of JPL and CTD *et al* (figure 16). These hinges were designed to link the main part of the satellite and two deployable panel wings on the two ends; the wings can control the yaw direction of the satellite by the deployment or packaging of the EMC hinge [144].

As the main energy generation component, the design and architecture of solar arrays are important factors to improve the efficiency of collecting energy. In the above-mentioned

structures, the deployment of solar arrays and panels are actuated by SMPC hinges; the deployed cells are limited and relatively small, so the power output is appropriate to space mission. Due to these drawbacks, another kinds of solar array, called Roll-out And Passively Deployed solar ARray (RAPDAR), has been developed by CTD [176–178]. In brief, RAPDAR consists of two EMC longerons/booms and several pieces of thin-film photovoltaic (TFPV) solar arrays, in which the booms actuate the solar array deployment and become the support structures of the solar array, as illustrated in figure 17 [176]. Due to the lower power-conversion efficiency compared with other kinds of solar arrays, the RAPDAR requires larger deployable areas to provide an equal total energy [177]. The use of EMC material can overcome this drawback, as demonstrated in the STEM boom section; similarly, the booms can be stowed before launch in the high-temperature state and the structure can be released and deployed by temperature or current, once in

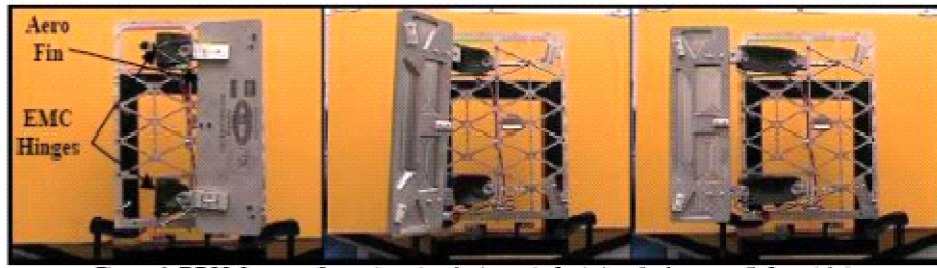


Figure 16. DINO Sat aero fin deployment process [144].

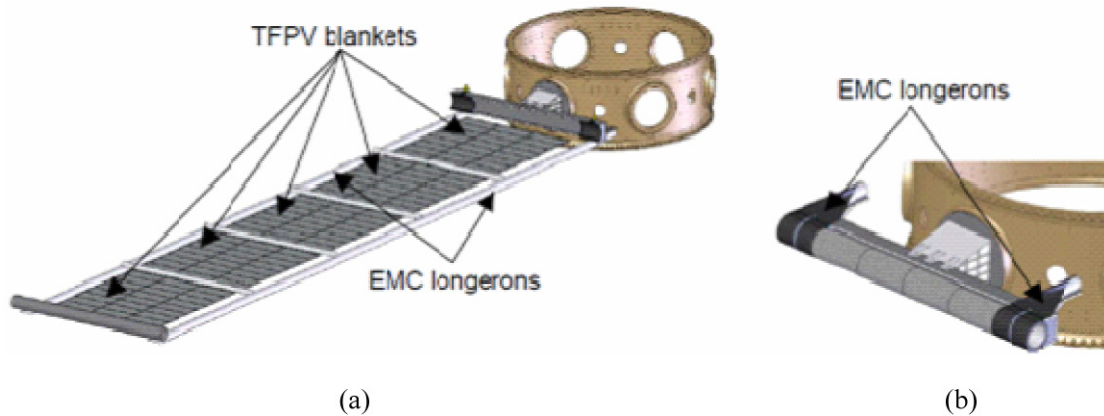


Figure 17. Schematic of RAPDAR concept: (a) deployed configuration, and (b) stowed configuration. Reused from [176] with permission from the authors.

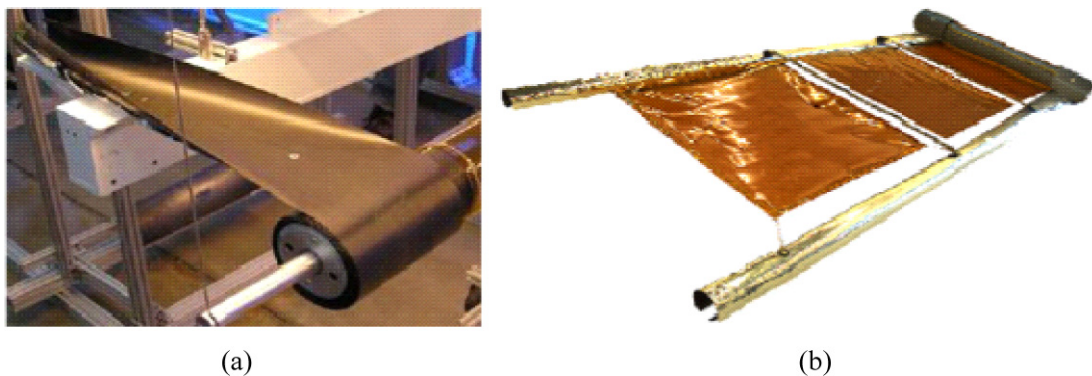


Figure 18. The deployment model of EMC boom: (a) EMC boom and (b) partially deployed model of solar arrays supported by the EMC boom. Reused from [177] with permission from the authors.

orbit [176–179]; the deployment processing is illustrated in figure 18 [177].

4.3.2. SMPC reflector antennas. The antenna is the important communication tool between the satellite and Earth in space, which can provide necessary information about space matter. Two main parameters measure the deployable antenna working properties: the reflector aperture and precision. However, the two parameters are contradictory in certain ways—the structure would be very complex if the two parameters could be satisfied simultaneously [180]. In addition, the weight and packaged volume of the deployable antenna are also considered in the design.

Researchers have proposed several types of structure models, such as the wrap-rib deployable antenna [181], the rigid-rib deployable antenna [182], the hinged-rib deployable antenna [183] and the tension truss antenna [184, 185]. All the aforementioned antennas have some drawbacks concerning the weight, reflector aperture or surface precision. As one of the ideal advanced materials, SMPCs can overcome these drawbacks and play an increasingly important role in space deployable antennas.

Yang *et al* developed a new type of mesh-surface antenna deployed using SMPC tapes, as demonstrated in figure 19. The structure essentially consists of six pieces of SMPC thin shell tapes, six tape linkers, six guided ribs, a steel supporter and six resistor heaters. The ground deployment experiment

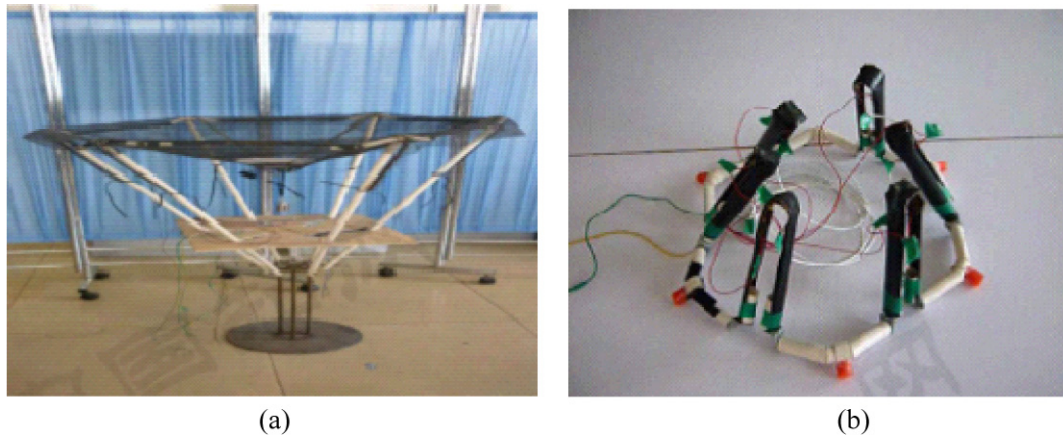


Figure 19. The space deployable mesh-surface antenna model: (a) deployed SMPC antenna and (b) packaged SMPC thin shells. Reused from [186] with permission from the authors.

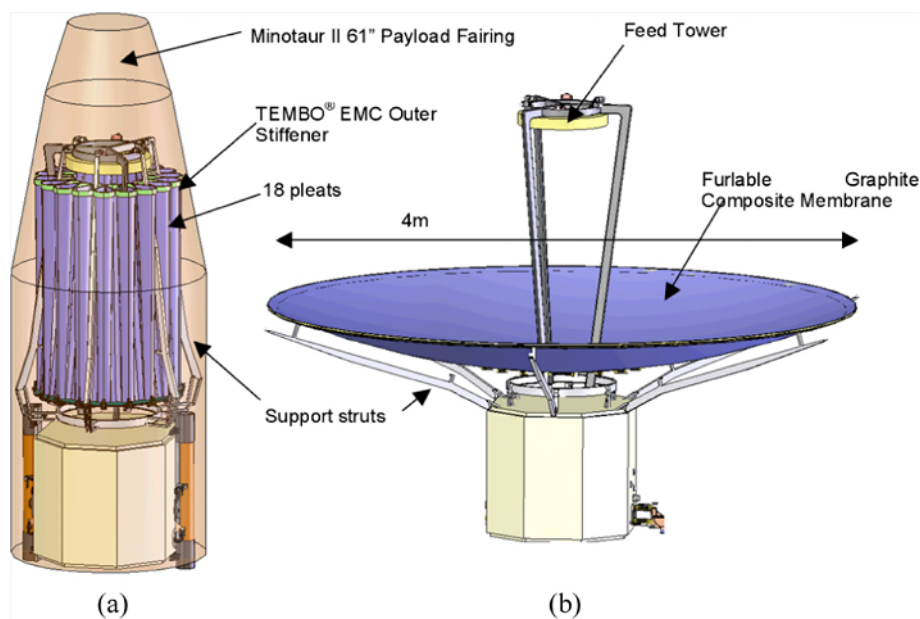


Figure 20. Solid-surface reflector developed by CTD: (a) the stowed state and (b) the deployed state. Reused from [188] with permission from the authors.

was performed using the heating of electricity. The results indicate that the SMPC antenna can be stowed into a small volume and be deployed completely by heating. Compared with traditional SMAs and mechanically deployable antennas, the structure is more lightweight and reduces the stowed strain energy; however, the surface precision is not significantly improved [186, 187].

CTD has developed a high-frequency solid-surface deployable reflector to better meet the requirement of future satellite missions in aerospace engineering, which mainly include: furlable graphite composite membrane, support struts and EMC outer stiffener, as shown in figure 20 [188]. The EMC stiffener is the key element of the reflector, which can provide deployment force for the reflector and become the important supporting structure after deployment. The result shows the EMC stiffener with high strain capability can be packaged into the stowed configuration under high

temperature and return to the deployed shape without large shock effect, when reheated above the EMC transition temperature [188].

Harris Company has been considering using the concept of SMPCs to design a new type of smart solid-surface deployable reflector called the Flexible Precision Reflector (FPR) and has created some models for deployment experiment, as shown in figure 21; the structure consists of two parts: the outer stiffener fabricated using an EMC material and a thin film surface reflector in the middle part. The structure is packaged in stowed configuration, which can be actuated to deploy in some manner, such as by using light or temperature change [189].

The inflatable antenna is an important type of deployable reflector, which is fabricated using flexible materials [190–194]. The antenna is packaged into a small volume before launch. When the spacecraft is in space, the antenna

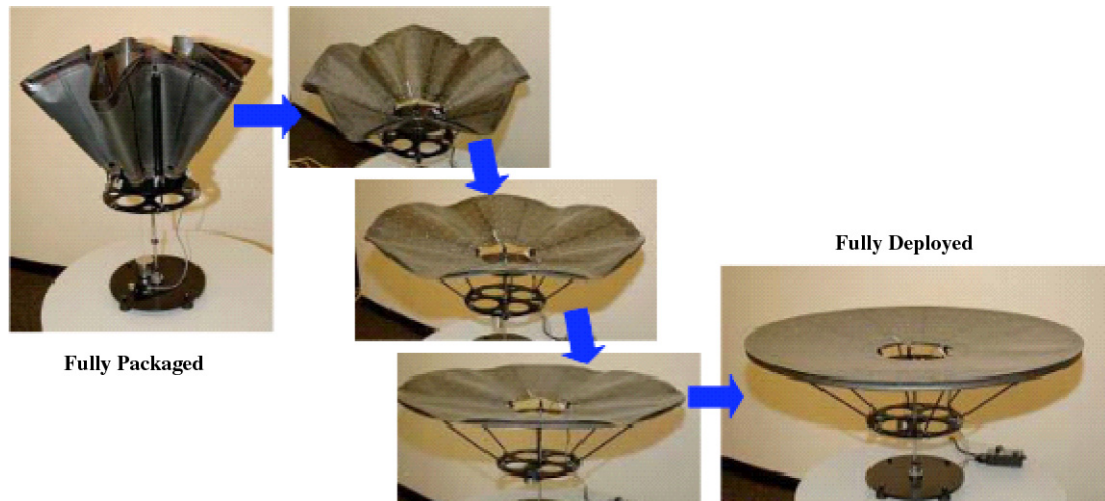


Figure 21. The deployment stages of Breadboard deployment. Reused from [189] with permission from the authors.

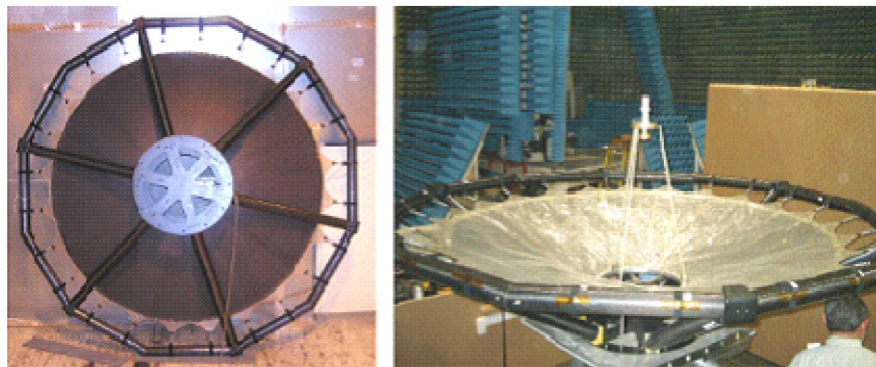


Figure 22. SMPC reflector for the hybrid inflatable antenna [191]. Reused with permission from the authors.

is released, inflated and hardens because of the physical or chemical effect. NASA successfully completed the in orbit experiment in 1996, the reflector provide sufficient surface reflector precision [190]. Today, SMPCs are considered for the fabrication of the main parts of the inflatable antenna to eliminate the air pressure leakage issue. A SMPC reflector model (2-m diameter) has been fabricated to validate the feasibility of SMPC as the supporting structure of a hybrid inflatable antenna, as shown in figure 22 [191]. These SMPC materials can significantly improve the structure application probability, via shape deformation and mechanical properties, and reduce the structural weight and cost effectively.

Yang *et al* have designed a class of inflatable reflectors to verify the good deployment mechanism [186]. The structure is fabricated using a carbon-fiber-reinforced SMPC material, with a parabolic-shaped surface and a 50-cm aperture. The four resistor heaters are stuck to the surface of the reflector and are used to actuate the structural deployment. The experimental results demonstrate that the structure can be deployed under the actuator of electricity and that it has a high surface precision. However, some drawbacks also need to be overcome such as the difficulty

of fabrication technology, large heating area and insufficient deployed–packaged ratio [186].

Recently, NASA has been developing a new type of radar antenna under the Earth Science Technology Program, which has a large deployable aperture and good emergency response ability; its shape is the Sunflower model, as shown in figure 23 [194]. After many fabrication, examinations and evaluations, the results demonstrate that the key factors of the production program rely on the application of SMPs and SMPCs in the design of rigidizable-inflatable (RI) structures at reasonable cost. The SMPC antenna not only satisfies the complex structure demand but is also lightweight and exhibits high reflector precision [194].

4.3.3. Morphing structures. The idea of morphing an aircraft's shape is far from new. The design inspiration originates from birds flying free in the air and changing their flight posture according to the air flow [195, 196]. However, traditional aircraft can only carry out a single missions in a flight, such as an F-17 being used for attack mission, or Boeing 747 used for long-distance transport mission [197]. To improve flight performance, morphing vehicles were introduced to overcome this problem and efficiently alleviate

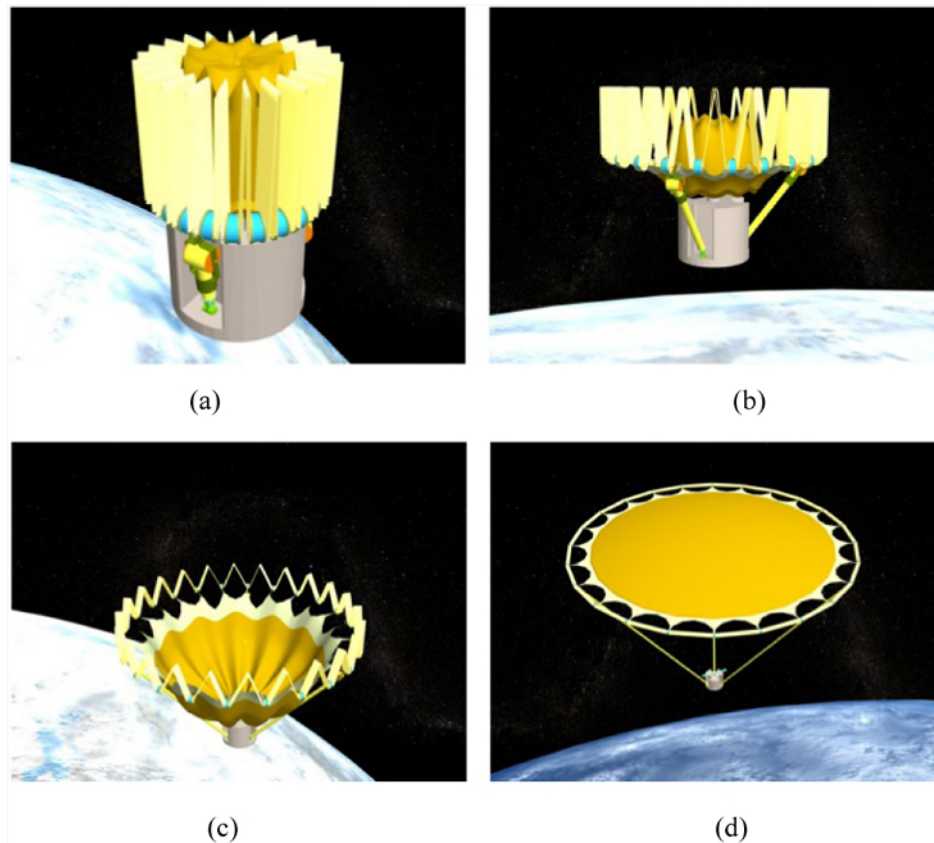


Figure 23. The deployment process of Sunflower reflector model: (a) the stowed state, (b) and (c) partial deployed state and (d) fully deployed state. Reused from [194] with permission from the authors.

structural deterioration [198, 199]. Today, researchers are greatly interested in designing new types of morphing wing skin; one of the branches involves SMPs and SMPCs, which can change their shape according to the temperature or other external stimulus and maintain normal efficiency.

Lockheed Martin has proposed a z-shape morphing vehicle concept and verified its flight properties through ground and wind tunnel tests of unmanned air vehicles (UAV) [200, 201]. Cornerstone Research Group (CRG) has improved the manufacture technique of SMPs for seamless skin: the wing skin can deform based on the packaging or deploying states of the hinge using SMPs at the conjunction parts [202].

Yu *et al* proposed the concept of a morphing wing consisting of SMPs/SMPCs and compared the deployment process of carbon-fiber-reinforced SMPs (CF-SMPs) with SMA-wire-reinforced SMP composites (SMA-wire-SMP) and elastic steel-slice-reinforced SMP composite (ESS-SMP) [203]. The results indicated that the SMA-wire-SMP and ESS-SMP have larger recovery speed than CF-SMPs due to the different reinforced materials. In addition, Yin *et al* developed the concept of a variable-camber wing and performed a related experiment to measure the deformation mechanism. The fiber Bragg grating (FBG) was selected to measure the deflection of the wing, as illustrated in figure 24 [204]. Bearing in mind that SMPCs possess variable mechanical properties under high/low temperature,

the variable stiffness styrene-based SMPC tube reinforced with carbon fiber was fabricated and embedded into the flexible silicon rubber skin. Experimental results showed that the variable-stiffness SMPC tube had significant effect on the deformation of the morphing skin: with increase of time, the deflection gradually grows [205, 206], as illustrated in figure 25. Moreover, Garcia *et al* give a good summary of the UAV morphing concepts, design, technologies and development state, especially in terms of technologies; many methods are described in detail to explain their advantages and disadvantages [207].

4.3.4. Expandable lunar habitat. If space exploration is conducted for a long time, a special shelter or habitat is needed to maintain basic life and avoid damage from ultraviolet radiation. To solve this problem, the development of space-deployable technology becomes important; its aim is to better reduce the occupied room in spacecraft and maximize the work volume in space. SMP/SMPC is one of the advanced materials to satisfy the purpose, as it can be packaged and stowed in a smaller volume and deployed using some stimuli in space to function [208, 209].

ILC Dover Company has teamed with NASA Langley Research Center to develop a type of inflatable expandable lunar habitat; the framework of the structure is composed of SMPCs, and the structure achieves the purpose of self-deployment and high extensive area. In addition, the model

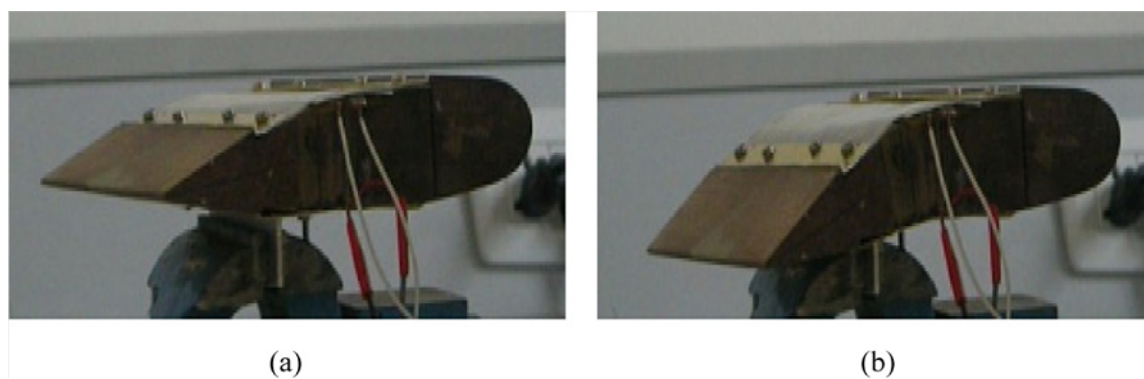


Figure 24. The deformation photograph of the variable-camber wing: (a) the original configuration and (b) the morphing configuration. Reused from [204], with permission from SPIE.

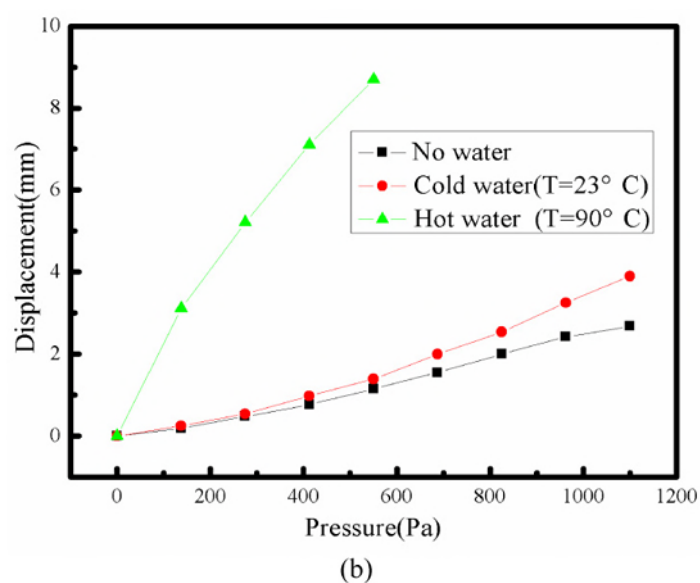
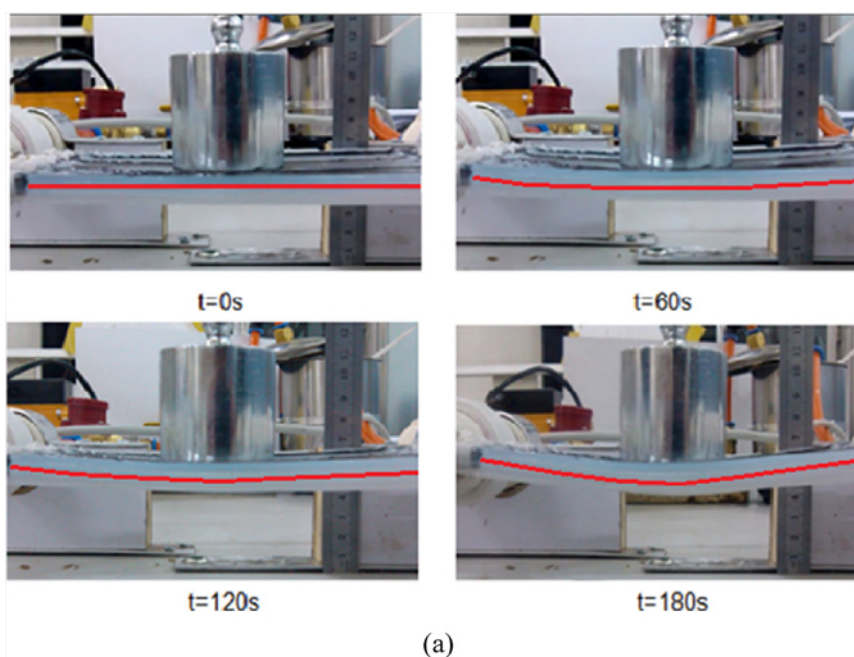


Figure 25. The deformation of morphing skin embedded into variable stiffness SMPC tube: (a) SMPC skin heating system, and (b) experimental curve of stress versus deformation of morphing skin [206].

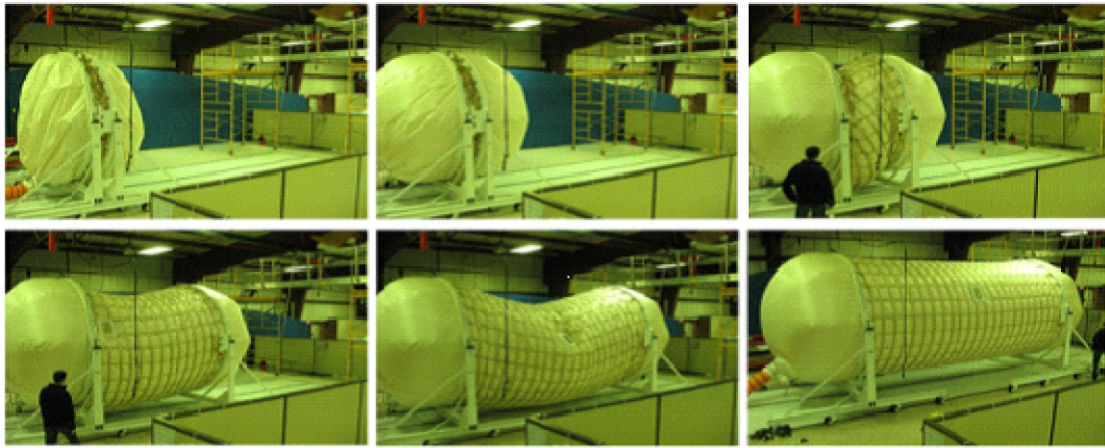


Figure 26. The deployment testing of expandable lunar habitat. Reused from [209] with permission from the authors.

was fabricated and the deployable process of the structure was examined in a ground experiment, as demonstrated in figure 26; the results indicated that the materials have good recovery properties under the air pressure deploying test [209]. Also, CRG has developed a self-constructing infrastructure for future moon and Mars missions to reduce the labor burden [210].

4.3.5. SMP and SMPC mandrels. Traditionally, there are two methods to overcome the fabrication problem of complex-curved structures: multi-piece metal mandrels and water-soluble mandrels. Although multi-piece metal mandrels can successfully satisfy the design precision, a significant amount of time, labor, energy, and cost is required to design, fabricate, assemble and demold these structures; on the other hand, the fabrication of water-soluble mandrels is relatively complexity. The main steps consist of preparing water-soluble materials (sand or salt) and a rigid support rod; forming pre-deformation shape of the structures; filament winding and curing; injecting water into the mandrel to dissolve the sand or salt; finally, the structure can be formed after cleaning the internal impurity [82]. Some companies (such as CTD) have fabricated linerless composite tanks using this method and analyzed the mechanical properties [211–213]. The disposable usage and residual noxious materials severely hinder the development of water-soluble mandrels. However, SMP mandrels or SMPC mandrels reinforced with a high strain fiber have the advantages of variable stiffness based on external temperature, a lower product cost, reusable usage and an easy demolding process, which is becoming a new developing direction of complex-curved structural manufacturing techniques.

CRG has fabricated a bottle-shaped mandrel and air-duct-shaped mandrel and verified the technique feasibility of SMP [82, 214–216]. Different types of SMP materials reinforced with fibers were produced to satisfy the various work environments in the company. Recently, Leng *et al* has investigated the mechanical properties of thermoset styrene SMP bottle-shaped mandrels and air-dust-shaped mandrels [217]. The results demonstrate the good deformation and reusable usage properties of the SMP mandrels: the

structures have good shape fixity and good shape recovery ratio after several cycles, and the deformation and demolding process are easily controlled with temperature.

5. Conclusions

As one kind of advanced smart material, SMPs and SMPCs are playing an increasingly important role in the aerospace field. In this review, a number of research findings have been introduced to show the current and potential applications of SMPCs in aerospace. Remarkable research works are focusing on the design and evaluation of SMPC components, such as SMPC hinge and boom. Different types of components have been developed to better meet the need of space deployable structures, such as solar arrays and deployable panels, reflector antennas and morphing structures.

The variable stiffness under different external stimuli is the most striking characteristic of SMPs and SMPCs. SMPC hinges/booms can be packaged and deployed to realize the shape fixity and shape recovery of components and structures, which can provide deploying force and damping during the deployment process and lock the shape at the end of deployment to support the deployed structures. However, there are some challenges to the applications of SMPC in aerospace, such as the limited types of high-temperature SMPC suitable for the harsh space environment.

Considering their unique advantages of light weight, low cost, low density, high strength–weight ratio, low part count, simple design, good manufacturability, high shape deformability and an easily tailorable glass transition temperature, SMPs and SMPCs are expected to develop in multiple dimensions and have great potential applications in aerospace in the near future.

Acknowledgments

This work is supported by the National Natural Science Foundation of China (Grant Nos 1122521, 11272106, 11102052).

References

- [1] Behl M and Lendlein A 2007 Shape memory polymers *Mater. Today* **10** 20–8
- [2] Behl M, Razzaq M Y and Lendlein A 2010 Multifunctional shape memory polymers *Adv. Mater.* **22** 3388–410
- [3] Ratna D and Karger-Kocsis J 2008 Recent advances in shape memory polymers and composites: a review *J. Mater. Sci.* **43** 254–69
- [4] Kunzleman J, Chung T, Mather P T and Weder C 2008 Shape memory polymers with built-in threshold temperature sensors *J. Mater. Chem.* **18** 1082–6
- [5] Mather P T, Luo X F and Rousseau I A 2009 Shape memory polymer research *Annu. Rev. Mater. Res.* **39** 445–71
- [6] Huang W M, Ding Z, Wang C C, Wei J, Zhao Y and Purnawali H 2010 Shape memory materials *Mater. Today* **13** 54–61
- [7] Xie T 2010 Tunable polymer multi-shape memory effect *Nature* **464** 267–70
- [8] Leng J S, Lan X, Liu Y J and Du S Y 2011 Shape memory polymers and their composites: stimulus methods and applications *Prog. Mater. Sci.* **56** 1077–135
- [9] Leng J S, Lv H B, Liu Y J, Huang W M and Du S Y 2009 Shape memory polymers—a class of novel smart materials *MRS Bull.* **34** 848–55
- [10] Hu J L, Zhu Y, Huang H H and Lu J 2012 Recent advances in shape memory polymers: structures, mechanism, functionality, modeling and applications *Prog. Polym. Sci.* **37** 1720–63
- [11] Tobushi H, Hara H, Yamada E and Hayashi S 1996 Thermomechanical properties in a thin film of shape memory polymer of polyurethane series *Smart Mater. Struct.* **5** 483–91
- [12] Tobushi H, Ito N, Takata K and Hayashi S 2000 Thermomechanical constitutive modeling of polyurethane series shape memory polymer *Mater. Sci. Forum* **327/328** 343–6
- [13] Wei Z G, Sandstrom R and Miyazaki S 1998 Shape memory materials and hybrid composites for smart systems—part I shape memory materials *J. Mater. Sci.* **33** 3743–62
- [14] Liu C, Qin H and Mather P T 2007 Review of progress in shape memory polymers *J. Mater. Chem.* **17** 1543–58
- [15] Gall K, Dunn M L, Liu Y P, Finch D, Lake M and Munshi N A 2002 Shape memory polymer nanocomposites *Acta Mater.* **50** 5115–26
- [16] Abrahamson E R, Lake M S, Munshi N A and Gall K 2003 Shape memory mechanics of an elastic memory composite resin *J. Intell. Mater. Syst. Struct.* **14** 623–32
- [17] Voit W, Ware T, Dasari R R, Smith P, Danz L, Simon D, Barlow S, Marder S R and Gall K 2010 High-strain shape memory polymers *Adv. Funct. Mater.* **20** 162–71
- [18] Hornbogen E 2006 Comparison of shape memory metals and polymers *Adv. Eng. Mater.* **8** 101–6
- [19] Wei K, Zhu G M, Tang Y S, Tian G M and Xie J Q 2012 Thermomechanical properties of shape-memory hydro-epoxy resin *Smart Mater. Struct.* **21** 055022
- [20] Fan M J, Yu H, Li X Y, Cheng J E and Zhang J Y 2013 Thermomechanical and shape memory properties of epoxy-based shape-memory polymer using diglycidyl ether of ethoxylated bisphenol-A *Smart Mater. Struct.* **22** 055034
- [21] Lv H B, Yu K, Sun S H, Liu Y J and Leng J S 2010 Mechanical and shape memory behavior of shape memory polymer composites with hybrid fillers *Polym. Int.* **59** 766–71
- [22] Wei Z G, Sandstrom R and Miyazaki S 1998 Shape memory materials and hybrid composites for smart systems—part II shape memory hybrid composites *J. Mater. Sci.* **33** 3763–83
- [23] Ohki T, Ni Q Q, Ohsako N and Iwamoto M 2004 Mechanical and shape memory behavior of composites with shape memory polymer *Composites A* **35** 1065–73
- [24] Zhang C S and Ni Q Q 2007 Bending behavior of shape memory polymer based laminates *Compos. Struct.* **78** 153–61
- [25] Zhou B and Liu Y J 2009 A glass transition model for shape memory polymer and its composite *Int. J. Mod. Phys. B* **23** 1248–53
- [26] Gunes I S and Jana S C 2008 Shape memory polymers and their nanocomposites: a review of science and technology of new multifunctional materials *J. Nanosci. Nanotechnol.* **8** 1616–37
- [27] Meng Q B and Hu J L 2009 A review of shape memory polymer composites and blends *Composites A* **40** 1661–72
- [28] Choi J T, Dao T D, Oh K M, Lee H I, Jeong H M and Kim B K 2012 Shape memory polyurethane nanocomposites with functionalized graphene *Smart Mater. Struct.* **21** 075017
- [29] Basit A, L'Hostis G and Durand B 2013 High actuation properties of shape memory polymer composite actuator *Smart Mater. Struct.* **22** 025023
- [30] Diorio A M, Luo X F, Lee K M and Mather P T 2011 A functionally graded shape memory polymer *Soft Matter* **7** 68–74
- [31] Luo X F and Mather P T 2010 Triple-shape polymeric composites *Adv. Funct. Mater.* **20** 2649–56
- [32] Xie T, Xiao X C and Yang T 2009 Revealing triple-shape memory effect by polymer bilayers *Macromol. Rapid Commun.* **30** 1823–7
- [33] Yu K, Xie T, Leng J S, Ding Y F and Qi H J 2012 Mechanisms of multi-shape memory effects and associated energy release in shape memory polymers *Soft Matter* **8** 5687–95
- [34] Xie T 2011 Recent advances in polymer shape memory *Polymer* **52** 4985–5000
- [35] Bellin I, Langer R and Lendlein A 2006 Polymeric triple-shape materials *Proc. Natl Acad. Sci. USA* **103** 18043–7
- [36] Behl M and Lendlein A 2010 Triple-shape polymers *J. Mater. Chem.* **20** 3335–45
- [37] Chen S J, Hu J L, Zhou H T and Zhu Y 2008 Two-way shape memory effect in polymer laminates *Mater. Lett.* **62** 4088–90
- [38] Westbrook K K, Mather P T, Parakh V, Dunn M L, Ge Q, Lee B M and Qi H J 2011 Two-way reversible shape memory effects in a free-standing polymer composite *Smart Mater. Struct.* **20** 065010
- [39] Wang Z D, Song W B, Ke L L and Wang Y S 2012 Shape memory polymer composite structures with two-way shape memory effects *Mater. Lett.* **89** 216–8
- [40] Kang T H, Lee J M, Yu W R, Youk J H and Ryu H W 2012 Two-way actuation behavior of shape memory polymer/elastomer core/shell composites *Smart Mater. Struct.* **21** 035028
- [41] Nji J and Li G Q 2010 A self-healing 3D woven fabric reinforced shape memory polymer composites for impact mitigation *Smart Mater. Struct.* **19** 035007
- [42] Nji J and Li G Q 2010 A biomimic memory polymer based self-healing particulate composite *Polymer* **51** 6021–9
- [43] John M and Li G Q 2010 Self-healing of sandwich structures with a grid stiffened shape memory polymer syntactic foam core *Smart Mater. Struct.* **19** 075013
- [44] Li G Q and John M 2008 A self-healing smart syntactic foam under multiple impacts *Compos. Sci. Technol.* **68** 3337–43
- [45] Squeo E A and Quadrini F 2010 Shape memory epoxy foams by solid-state foaming *Smart Mater. Struct.* **19** 105002
- [46] Quadrini F, Santo L and Squeo E A 2012 Shape memory epoxy foams for space applications *Mater. Lett.* **69** 20–3

- [47] Santo L, Quadri F, Squeo E A, Dolce F, Mascetti G, Berolotto D, Villadei W, Ganga P L and Zolesi V 2012 Behavior of shape memory epoxy foams in microgravity: experimental results of STS-134 mission *Micrograv. Sci. Technol.* **24** 287–96
- [48] Lake M S and Campbell D 2004 The fundamentals of designing deployable structures with elastic memory composites *2004 IEEE Aerospace Conf. Proc.* vol 4, pp 2745–56
- [49] Sokolowski W M and Tan S C 2007 Advanced self-deployable structures for space applications *J. Spacecr. Rockets* **44** 750–4
- [50] Baghani M, Naghdabadi R and Arghavani J 2012 A semi-analytical study on helical springs made of shape memory polymer *Smart Mater. Struct.* **21** 045014
- [51] Lv H B, Leng J S and Du S Y 2009 A survey of adaptive materials and structures research in China *50th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Palm Springs, CA, May)*
- [52] Tan Q, Liu L W, Liu Y J and Leng J S 2013 Post buckling analysis of the shape memory polymer composite laminate bonded with alloy film *Comp. B: Eng.* at press
- [53] Leng J S, Liu L W, Lv H B and Liu Y J 2012 Applications for shape memory polymer composite in aerospace *JEC Compos.* **72** 56–8
- [54] Lendlein A and Langer R 2002 Biodegradable, elastic shape-memory polymers for potential biomedical applications *Science* **296** 1673–6
- [55] Lendlein A and Kelch S 2005 Shape-memory polymers as stimuli-sensitive implant materials *Clin. Hemorheol. Microcirc.* **32** 105–16
- [56] Wischke C, Neffe A T, Steuer S and Lendlein A 2009 Evaluation of a degradable shape-memory polymer network as matrix for controlled drug release *J. Control. Release* **138** 243–50
- [57] Wischke C, Neffe A T, Steuer S and Lendlein A 2010 Comparing techniques for drug loading of shape memory polymer networks-effect on their functionalities *Eur. J. Pharm. Sci.* **41** 136–47
- [58] Metzger M F, Wilson T S, Schumann D, Matthews D L and Maitland D J 2002 Mechanical properties of mechanical actuator for treating ischemic stroke *Biomed. Microdevices* **4** 89–96
- [59] Baer G, Wilson T S, Maitland D J and Matthews D L 2006 Shape memory polymer neurovascular stents *J. Investig. Med.* **54** S162
- [60] Ji F L, Zhu Y, Hu J L, Liu Y, Yeung L Y and Ye G D 2006 Smart polymer fibers with shape memory effect *Smart Mater. Struct.* **15** 1547–54
- [61] Mondal S and Hu J L 2006 Temperature stimulating shape memory polyurethane for smart clothing *Indian J. Fiber Text. Res.* **31** 66–71
- [62] Zhu Y, Hu J L, Luo H S, Young R J, Deng L B, Zhang S, Fan Y and Ye G D 2012 Rapid switchable water-sensitive shape memory cellulose/elastomer nano-composites *Soft Matter* **8** 2509–17
- [63] Vili Y Y F C 2007 Investigating smart textiles based on shape memory materials *Text. Res. J.* **77** 290–300
- [64] Kobayashi K and Hayashi S 1992 Shape memory fibrous sheet and method of imparting shape memory property to fibrous sheet product *US Patent Specification* 5098776
- [65] Browne A L, Johnson N L and Namuduri C S 2004 Electrostatically releasable fastening system and method of use *US Patent Specification* 6944920
- [66] Browne A L and Johnson N L 2008 Hood assembly utilizing active materials based mechanisms *US Patent Specification* 20080197674
- [67] Brei D, Redmond J, Wilmot N A, Browne A L, Johnson N L and Jones G L 2006 Hood lift mechanisms utilizing active materials and methods of use *US Patent Specification* 7063377 B2
- [68] www.acemr.eu/uploads/media/Trendstudy_ACEMR_Designmaterials_01.pdf
- [69] Lin J R and Chen L W 1999 The mechanical viscoelastic model and WLF relationship in shape memorized linear ether type polyurethanes *J. Polym. Res.* **6** 35–40
- [70] McClung A J W, Tandon G P and Baur J W 2012 Strain rate and temperature-dependent tensile properties of an epoxy-based, thermosetting, shape memory polymer *Mech. Time-Dep. Mater.* **16** 205–21
- [71] McClung A J W, Tandon G P and Baur J W 2013 Deformation rate-, hold time, and cycle-dependent shape memory performance of Veriflex-E resin *Mech. Time-Dep. Mater.* **17** 39–52
- [72] Hu J L 2007 *Shape Memory Polymers and Textiles* (Cambridge: Woodhead)
- [73] Xie T and Rousseau I A 2009 Facile tailoring of thermal transition temperatures of epoxy shape memory polymers *Polymer* **50** 1852–6
- [74] Rousseau I A and Xie T 2009 Shape memory epoxy: a systematic study of their performance *Proc. SPIE* **7289** 72890X
- [75] Leng J S, Wu X L and Liu Y J 2009 Effect of a linear monomer on the thermomechanical properties of epoxy shape memory polymer *Smart Mater. Struct.* **18** 095031
- [76] Li F K and Larock R C 2003 New soybean oil–styrene–divinylbenzene thermosetting copolymers. VI. Time–temperature–transformation cure diagram and the effect of curing conditions on the thermoset properties *Polym. Int.* **52** 126–32
- [77] Zhang D W, Liu Y J, Yu K and Leng J S 2011 Influence of cross-linking agent on the thermomechanical properties and shape memory effect of styrene shape memory polymer *J. Intell. Mater. Syst. Struct.* **22** 2147–54
- [78] Shumaker J A, McClung A J W and Baur J W 2012 Synthesis of high temperature polyaspartimide-urea based shape memory polymers *Polymer* **53** 4637–42
- [79] Biju R, Gouri C and Nair C P R 2011 Shape memory polymers based on cyanate ester–epoxy–poly (tetramethyleneoxide) co-reacted system *Eur. Polym. J.* **48** 499–511
- [80] Xie F, Huang L N, Liu Y J and Leng J S 2012 Modified shape memory cyanate polymers with a wide range of high glass transition temperatures *Proc. SPIE* **8342** 834210
- [81] www.ctd-materials.com/papers/menu.php
- [82] Everhart M C, Nickerson D M and Hreha R D 2006 High-temperature reusable shape memory polymer mandrels *Proc. SPIE* **6171** 61710K
- [83] Cadogan D P, Scarborough S E, Ling J K and Sapna G H III 2002 Shape memory composite development for use in gossamer space inflatable structures *43rd AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Denver, CO, April)*
- [84] Wang Z D, Li D F, Xiong Z Y and Chang R N 2008 Modeling thermomechanical behaviors of shape memory polymer *J. Appl. Polym. Sci.* **113** 651–6
- [85] Zhang Q and Yang Q S 2012 Recent advance on constitutive models of thermal-sensitive shape memory polymers *J. Appl. Polym. Sci.* **123** 1502–8
- [86] Tobushi H, Hashimoto T, Hayashi S and Yamada E 1997 Thermomechanical constitutive modeling in shape memory polymer of polyurethane series *J. Intell. Mater. Syst. Struct.* **8** 711–8
- [87] Tobushi H, Okumura K, Hayashi S and Ito N 2001 Thermomechanical constitutive model of shape memory polymer *Mech. Mater.* **33** 545–54
- [88] Bhattacharyya A and Tobushi H 2000 Analysis the isothermal mechanical response of a shape memory polymer rheological model *Polym. Eng. Sci.* **40** 2498–510
- [89] Liu Y P, Gall K, Dunn M L, Greenberg A R and Diani J 2006 Thermomechanics of shape memory polymers:

- uniaxial experiments and constitutive modeling *Int. J. Plast.* **22** 279–313
- [90] Liu Y P 2004 *Thermomechanical Behavior of Shape Memory Polymers* (Denver, CO: University of Colorado)
- [91] Leng J S and Lau K T 2010 *Multifunctional Polymer Nanocomposites* (London: CRC Press/Taylor & Francis)
- [92] Sun L, Huang W M, Ding Z, Zhao Y, Wang C C, Purnawali H and Tang C 2012 Stimulus-responsive shape memory materials: a review *Mater. Des.* **33** 577–640
- [93] Meng H and Hu J L 2010 A brief review of stimulus-active polymers responsive to thermal, light, magnetic, electric, and water/solvent stimuli *J. Intell. Mater. Syst. Struct.* **21** 859–85
- [94] Hu J L, Meng H P, Li G Q and Ibekwe S I 2012 A review of stimuli-responsive polymers for smart textile applications *Smart Mater. Struct.* **21** 053001
- [95] Meng H P and Li G Q 2013 A review of stimuli-responsive shape memory polymer composites *Polymer* **54** 2199–221
- [96] Qi H J, Dunn M L, Long K, Castro F and Shandas R 2007 Thermomechanical indentation of shape memory polymers *Proc. SPIE* **6526** 652615
- [97] Castro F, Westbrook K K, Long K N, Shandas R and Qi H J 2010 Effect of thermal rates on the thermomechanical behavior of amorphous shape memory polymers *Mech. Time-Dep. Mater.* **14** 219–41
- [98] Liu Y P, Gall K, Dunn M L and McCluskey P 2004 Thermomechanics of shape memory polymer nanocomposites *Mech. Mater.* **36** 929–40
- [99] Gall K, Yakacki C M, Liu Y P, Shandas R, Willett N and Anseth K S 2005 Thermomechanics of the shape memory effect in polymers for biomedical applications *J. Biomed. Mater. Res. A* **73A** 339–48
- [100] Baer G, Wilson T S, Matthews D L and Maitland D J 2007 Shape memory behavior of thermally stimulated polyurethane for medical applications *J. Appl. Polym. Sci.* **103** 3882–92
- [101] Yu K, Liu Y J, Liu Y, Peng H X and Leng J S 2013 Mechanical and shape recovery properties of shape memory polymer composite embedded with cup stacked carbon nanotubes *J. Int. Mater. Syst. Struct.* accepted
- [102] Liu Y J, Lv H B, Lan X, Leng J S and Du S Y 2009 Review of electro-active shape memory polymer composite *Compos. Sci. Technol.* **69** 2064–8
- [103] Cho J W, Kim J W, Jung Y C and Coo N S 2005 Electroactive shape memory polyurethane composites incorporating carbon nanotubes *Macromol. Rapid Commun.* **26** 412–6
- [104] Paik I H, Coo N S, Jung Y C and Cho J W 2006 Development and application of conducting shape memory polyurethane actuators *Smart Mater. Struct.* **15** 1476–82
- [105] Mondal S and Hu J L 2006 Shape memory studies of functionalized MWNT-reinforced polyurethane copolymers *Iran. Polym. J.* **15** 135–42
- [106] Meng Q H, Hu J L and Mondal S 2008 Thermal sensitive shape recovery and mass transfer properties of polyurethane/modified MWNT composite membranes synthesized via *in situ* solution pre-polymerization *J. Membr. Sci.* **319** 102–10
- [107] Lv H B, Liu Y J, Gou J, Leng J S and Du S Y 2010 Electrical properties and shape memory behavior of self-assembled carbon nanofiber nanopaper incorporated with shape memory polymer *Smart Mater. Struct.* **19** 075021
- [108] Lv H B, Liu Y J and Leng J S 2012 Carbon nanopaper enabled shape memory polymer composites for electrical actuation and multifunctionalization *Macromol. Mater. Eng.* **297** 1138–47
- [109] Leng J S, Lan X, Liu Y J and Du S Y 2009 Electroactive thermoset shape memory polymer nanocomposite filled with nanocarbon powders *Smart Mater. Struct.* **18** 074003
- [110] Lan X, Leng J S, Liu Y J and Du S Y 2008 Investigate of electrical conductivity of shape memory polymer filled with carbon black *Adv. Mater. Sci.* **47–50** 714–7
- [111] Leng J S, Lan X, Liu Y J, Du S Y, Huang W M, Liu N, Phee S J and Yuan Q 2008 Electrical conductivity of thermoresponsive shape-memory polymer with embedded micron sized Ni powder chains *Appl. Phys. Lett.* **92** 014104
- [112] Leng J S, Huang W M, Lan X, Liu Y J and Du S Y 2008 Significantly reducing electrical resistivity by forming conductive Ni chains in a polyurethane shape memory polymer/carbon black composite *Appl. Phys. Lett.* **92** 204101
- [113] Leng J S, Lv H B, Liu Y J and Du S Y 2007 Electroactivate shape-memory polymer filled with nanocarbon particles and short carbon fibers *Appl. Phys. Lett.* **91** 144105
- [114] Leng J S, Lv H B, Liu Y J and Du S Y 2008 Synergic effect of carbon black and short carbon fiber on shape memory polymer actuation by electricity *J. Appl. Phys.* **104** 104917
- [115] Lv H B, Liu Y J, Gou J H, Leng J S and Du S Y 2010 Synergistic effect of carbon nanofiber and carbon nanopaper on shape memory polymer composite *Appl. Phys. Lett.* **96** 084102
- [116] Gunes I S, Jimenez G A and Jana S C 2009 Carbonaceous fillers for shape memory actuation of polyurethane composites by resistive heating *Carbon* **47** 981–97
- [117] Yu K, Lv H B, Liu Y J and Leng J S 2010 Sensing and actuating capabilities of shape memory polymer composite integrated with hybrid filler *Smart Mater. Struct.* **19** 065014
- [118] Lendlein A, Jiang H Y, Junger O and Langer R 2005 Light-induced shape memory polymers *Nature* **434** 879–82
- [119] Jiang H Y, Kelch S and Lendlein A 2006 Polymer move in response to light *Adv. Mater.* **18** 1471–5
- [120] Behl M and Lendlein A 2007 Actively moving polymers *Soft Matter* **3** 58–67
- [121] Leng J S, Zhang D W, Liu Y J, Yu K and Lan X 2010 Study on the activation of styrene-based shape memory polymer by medium infrared laser light *Appl. Phys. Lett.* **96** 111905
- [122] Leng J S, Wu X L and Liu Y J 2009 Infrared light-active shape memory polymer filled with nanocarbon particles *J. Appl. Sci.* **114** 2455–60
- [123] Small W, Wilson T S, Benett W J, Loge J and Maitland D J 2005 Laser-activated shape memory polymer intravascular thrombectomy device *Opt. Express* **13** 8204–13
- [124] Maitland D J, Small W, Ortega J M, Buckley P R, Rodriguez J, Hartman J and Wilson T S 2007 Prototype laser-activated shape memory polymer foam device for embolic treatment of aneurysms *J. Biomed. Opt.* **12** 030504
- [125] Bare J M, Small W, Wilson T S, Benett W J, Matthews D L, Hartman J and Maitland D J 2007 Fabrication and *in vitro* deployment of a laser-activated shape memory vascular stent *Biomed. Eng. Online* **6** 43
- [126] Yu K, Westbrook K K, Kao P H, Leng J S and Qi H J 2012 Design considerations for shape memory polymer composites with magnetic particles *J. Compos. Mater.* **47** 51–63
- [127] Schmidt A M 2006 Electromagnetic activation of shape memory polymer networks containing magnetic nanoparticles *Macromol. Rapid Commun.* **27** 1168–72
- [128] Vialle G, Prima M D, Hocking E, Gall K, Garrestani H, Sanderson T and Arzberger S C 2009 Remote activation of nanomagnetite reinforced shape memory polymer foam *Smart Mater. Struct.* **18** 115014
- [129] Yacacki C M, Satarkar N S, Gall K, Likos R and Hilt J Z 2009 Shape memory polymer networks with Fe₃O₄ nanoparticle for remote activation *J. Appl. Polym. Sci.* **112** 3166–76

- [130] Weigel T H, Mohr R and Lendlein A 2009 Investigation of parameters to achieve temperatures required to initiate the shape memory effect of magnetic nanocomposites by inductive heating *Smart Mater. Struct.* **18** 025011
- [131] Razzaq M Y, Behl M and Lendlein A 2012 Magnetic memory effect of nanocomposites *Adv. Funct. Mater.* **22** 184–91
- [132] Yang B, Huang W M, Li C, Lee C M and Li L 2004 On the effect of moisture in a polyurethane shape memory polymer *Smart Mater. Struct.* **13** 191–5
- [133] Huang W M, Yang B, An L, Li C and Chan Y S 2005 Water-driven programmable polyurethane shape memory polymer: demonstration and mechanism *Appl. Phys. Lett.* **86** 114105
- [134] Wang C C, Huang W M, Ding Z, Zhao Y and Purnawali H 2012 Cooling/water-responsive shape memory hybrids *Compos. Sci. Technol.* **72** 1178–82
- [135] Lv H B, Liu Y J, Zhang D X, Leng J S and Du S Y 2008 Solution-responsive shape-memory polymer driven by forming hydrogen bonding *Adv. Mater. Res.* **47–50** 258–61
- [136] Lv H B, Leng J S, Liu Y J and Du S Y 2008 Shape-memory polymer in response to solution *Adv. Eng. Mater.* **10** 592–5
- [137] www.lpi.usra.edu/meetings/LEA/presentations/wed_am/1_Mazur_Space_Weather_Impacts.pdf
- [138] <http://webserver.dmt.upm.es/~isidoro/tc3/Space%20environment.pdf>
- [139] http://maelabs.ucsd.edu/mae155/classes/wi_05/space%20envt_nasa%20rp1390.pdf
- [140] Fulcher J T, Lu Y C, Tandon G P and Foster D C 2010 Thermomechanical characterization of environmentally conditioned shape memory polymer using nanoindentation *Proc. SPIE* **7644** 76440F
- [141] Leng J S, Xie F, Wu X L and Liu Y J 2013 Effect of the γ -radiation on the properties of epoxy-based shape memory polymers *J. Int. Mater. Syst. Struct.* accepted
- [142] Arzberger S C, Munshi N A, Lake M S, Wintergerst J, Varlese S and Ulmer M P 2003 Elastic memory composite technology for thin, lightweight space and ground-based deployable mirrors *Proc. SPIE* **5179** 143–54
- [143] Conley P L 1998 *Space Vehicle Mechanisms: Element and Successful Design* (New York: Wiley)
- [144] Arzberger S C *et al* 2005 Elastic memory composites (EMC) for deployable industrial and commercial applications *Proc. SPIE, Smart Structures and Materials 2005: Industrial and Commercial Applications of Smart Structures Technologies (San Diego, CA, March)* vol 5762, pp 35–47
- [145] www.techbriefs.com/component/content/article/14212
- [146] Beavers F L, Munshi N A, Lake M S, Maji A, Carpenter B, Rawal S and Qassim K 2002 Design and testing of an elastic memory composite deployment hinge for spacecraft *43th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Denver, CO, April)*
- [147] Tupper M, Munshi N, Beavers F, Gall K, Mikulas M and Meink T 2001 Development in elastic memory composite materials for spacecraft structures *2001 IEEE Aerospace Conf. Proc. (Big Sky, MT, March)*
- [148] Vyvyan W W 1968 Self-actuating, self-locking hinge *US Patent Specification* 3386128
- [149] Schwartz S S and Rubin C P 1972 Self-actuating, self-locking flexible hinge *US Patent Specification* 3670358
- [150] Chiappetta F R, Frame C L and Johnson K L 1993 Hinge element and deployable structures including hinge element *US Patent Specification* 5239793
- [151] Seffen K A and Pellegrino S 1999 Deployment dynamics of tape spring *Proc. R. Soc. A* **455** 1003–48
- [152] Seffen K A, Pellegrino S and Parks G T 2000 Deployment of a panel by tape spring hinges *Proc. IUTAM Symp. on Deployable Structures: Theory and Applications* vol 80, pp 355–64
- [153] Soykasap O 2007 Analysis of tape spring hinges *Int. J. Mech. Sci.* **49** 853–60
- [154] Francis W, Lake M S, Mallick K, Freebury G E and Maji A 2003 Development and testing of a hinge/actuator incorporating elastic memory composites *44th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Norfolk, VA, April)*
- [155] Leng J S and Du S Y 2010 *Shape Memory Polymer and Multifunctional Nanocomposite* (Boca Raton, FL: CRC Press) (London: CRC Press/Taylor and Francis)
- [156] Lan X, Liu Y J, Lv H B, Wang X H, Leng J S and Du S Y 2009 Fiber reinforced shape memory polymer composite and its application in a deployable hinge *Smart Mater. Struct.* **18** 024002
- [157] Maehl R C 1984 Extendible tubular booms for remote sensors *US Patent Specification* 4446466
- [158] Annon 1971 *Tubular spacecraft booms (extendible, Reel Stored)* SP-8065, NASA
- [159] Crawford R F 1971 Strength and efficiency of deployable booms for space applications *AAS/AIAA Variable Geometry and Expandable Structures Conf. (Anaheim, CA, April)* p 71396
- [160] Harvey T J, Harvey T J, Hinkle J, Stamm S and Ruhl E 2008 K-truss deployable boom system *US Patent Specification* 20080283670
- [161] www.northropgrumman.com/BusinessVentures/AstroAerospace/Products/Pages/STEM.aspx
- [162] Keller P N, Lake M S, Francis W, Barrett R, Wintergerst J, Harvey J, Ruhl E, Winter J, Scherbarch M R and Murphey T W 2004 Development of a deployable boom for microsatellites using elastic memory composite material *45th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Palm Springs, CA, April)*
- [163] Fetchko P, Sellers J J, Spanjers G, Scherbarch M, Winters J, Barrett R, Lake M S and Keller P N 2004 Deployment optimization of a boom for FalconSAT-3 using elastic memory materials *18 Annu. AIAA/USU Conference on Small Satellites*
- [164] Campbell D, Lake M S, Scherbarch M S, Nelson E and Six R W 2005 Elastic memory composite material: an enabling technology for future furlable space structures *46th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Austin, TX, April)*
- [165] Lake M S, Munshi N A, Tupper M L and Meink T 2001 Application of elastic memory composite materials to deployable space structures *AIAA Space 2001 Conf. and Exposition (Albuquerque, NM, Aug.)*
- [166] Campbell D, Lake M S, Hazelton C S, Wilder N and Spence B 2004 Development of a shape memory coilable boom using elastic memory composite material *9th Bienial Int. Conf. on Engineering, Construction and Operations in Challenging Environment: Earth and Space (Houston, TX, March)*
- [167] Schultz M R, Hulse M J and Keller P N 2006 Neutrally stable composite tape springs *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Newport, RI, May)*
- [168] Hazenlton C S, Gall K R, Abrahamson E R, Denis R J and Lake M S 2003 Development of a prototype elastic memory composite STEM for large space structures *44th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Norfolk, VA, April)* p 1977

- [169] Francis W H, Lake M S and Steven M J 2006 A review of classical fiber microbuckling analytical solutions for use with elastic memory composites *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Newport, RI, May)*
- [170] Hulse M J, Campbell D, Ryan K C J, Haynes M M and Francis W H 2007 Nonlinear effects in unidirectional elastic memory composite material *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Waikiki, HI, April)*
- [171] Francis W H, Lake M S, Schultz M R, Campbell D, Dunn M and Jerry Q H 2007 Elastic memory composite microbuckling mechanics: closed-form model with empirical correlation *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Waikiki, HI, April)*
- [172] Lan X, Liu L W, Liu Y J, Leng J S and Du S Y 2013 Post microbuckling mechanics of fiber-reinforced shape memory polymer undergoing flexure deformation *Mech. Mater.* [at press](#)
- [173] Kuchler G, Muller J and Koker I 2005 COMED-flexible solar generator *Proc. 7th European Space Power Conf. (Stresa, May)*
- [174] Barrett R, Francis W, Abrahamson E and Lake M S 2006 Qualification of elastic memory composite hinges for spaceflight application *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Newport, RI, May)*
- [175] Barrett R, Taylor R, Keller P N, Lake M S, Stern T, Freebury G and Beidleman N 2007 Design of a solar array to meet the standard bus specification for operation responsive space *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Waikiki, HI, April)*
- [176] Schultz M R, Francis W H, Campbell D and Lake M S 2007 Analysis techniques for shape memory composite structures *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Waikiki, HI, April)*
- [177] Taylor R M, Abrahamson E, Barrett R, Codell D E and Keller P N 2007 Passive deployment of an EMC boom using radiant energy in thermal vacuum *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Waikiki, HI, April)*
- [178] Barrett R, Campbell D, Lake M S and Taylor R 2006 Development of a passively deployed roll-out solar array *4th Int. Energy Conversion and Engineering Conf. (San Diego, CA, June)*
- [179] Campbell D, Barrett R, Lake M S and Abramson E 2006 Development of a novel, passively deployed roll-out solar array *2006 IEEE Aerospace Conf. (Big Sky, March)*
- [180] Luo Y and Duan B Y 2005 The study of structure of space deployed antenna *Electro-Mech. Eng.* **21** 30–4
- [181] Im E, Thomson M, Fang H F, Pearson J C, James M and Lin J K 2007 Prospects of large deployable reflector antennas for a new generation or geostationary Doppler weather radar satellites *AIAA Space Conf. (Long Beach, CA, Sept. 18–20)*
- [182] Gibbons R C 1995 Potential future applications for the tracking and data relay satellite II (TDRS II) system *Acta Astronaut.* **35** 537–45
- [183] Gunnar T 2002 *Deployable Tensegrity Structures for Space Applications* (Stockholm: Royal Institute of Technology)
- [184] Hanayama E, Kuroda S, Takano T, Kobayashi H and Kawaguchi N 2004 Characteristics of the large deployable antenna on HALCA satellite in orbit *IEEE Trans. Antennas Propag.* **52** 1777–82
- [185] Takano T, Miura K, Natori M, Hanayama E, Inoue T, Noguchi T, Miyahara N and Nakaguro H 2004 Deployable antenna with 10-m maximum diameter for space use *IEEE Trans. Antennas Propag.* **52** 2–11
- [186] Yang P 2011 Research on the structure of space deployable antenna based on shape memory polymer composites (China: Harbin Institute of Technology)
- [187] Leng J S, Liu Y J, Lan X and Yang P 2010 A deployable reflector and skeleton frame fabrication based on shape memory polymer composites *Chinese Patent Specification* 201010180826.2
- [188] Barrett R, Taylor R, Keller P N, Codell D and Adams L 2007 Deployable reflectors for small satellites *21th Annual Conf. Smart Satellites (Logan, UT, Aug.)*
- [189] Keller P N, Lake M S, Codell D, Barrett R, Taylor R and Schultz M R 2006 Development of elastic memory composite stiffeners for a flexible precision reflector *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Newport, RI, May)* vol 10, pp 6984–94
- [190] Freeland R E and Bilyeu C D 1992 In-step inflatable antenna experiment *43rd Congr. of the Int. Astronautical Federation (Washington, DC)*
- [191] Lin J K H, Knoll C F and Willey C E 2006 Shape memory rigidizable inflatable (RI) structures for large space systems applications *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Newport, RI, May)* vol 5, pp 3695–704
- [192] Willey C E, Schulze R C, Bokulic R S, Lin J K H, Cadogan D P and Knoll C F 2001 A hybrid inflatable dish antenna system for spacecraft *42nd AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Seattle, WA, April)*
- [193] Darooka D K and Jensen D W 2001 Advanced space structure concepts and their development *42nd AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics and Materials Conf. (Seattle, WA, April)* vol 1, pp 562–71
- [194] John L, Houfei F, Eastwood I and Ubaldo Q 2006 Concept study of a 35-m spherical reflector system for NEXRAD in space application *47th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Newport, RI, May)* vol 1, pp 62–73
- [195] Barbarino S, Bilgen O, Ajaj R M, Firsiwell M I and Inman D J 2011 A review of morphing aircraft *J. Intell. Mater. Syst. Struct.* **22** 823–77
- [196] Bubert E A, Woods B K S, Lee K, Kothera C S and Wereley N M 2010 Design and fabrication of a passive 1D morphing aircraft skin *J. Intell. Mater. Syst. Struct.* **21** 1699–717
- [197] Rauscher S G 2006 Testing and analysis of shape memory polymers for morphing aircraft skin application *Dissertation for the Master Degree in Mechanical Engineering* USA, University of Pittsburgh
- [198] Gevers D E 1997 Multi-purpose aircraft *US Patent Specification* 5645250
- [199] Thill C, Etches J, Bond I, Potter K and Weaver P 2008 Morphing skins *Aeronaut. J.* **112** 117–39
- [200] Love M H, Zink P S, Stroud R L, Bye D R, Rizk S and White D 2007 Demonstration of morphing technology through ground and wind tunnel tests *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Waikiki, HI, April)* vol 1, pp 337–48
- [201] Ivanko T, Scott R, Love M, Zink S and Weisshaar T 2007 Validation of the Lockheed Martin morphing concept with wind tunnel testing *48th AIAA/ASME/ASCE/AHS/ASC*

- Structures, Structural Dynamics, and Materials Conf. (Waikiki, HI, April)* vol 7, pp 6464–80
- [202] Bye D R and McClure P D 2007 Design of a morphing vehicle *48th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Waikiki, HI, April)* vol 1, pp 321–36
- [203] Yu K, Yin W L, Sun S H, Liu Y J and Leng J S 2009 Design and analysis of morphing wing based on SMP composite *Proc. SPIE* **7290** 72900S
- [204] Yin W L, Fu T, Liu J C and Leng J S 2009 Structural shape sensing for variable camber wing using FBG sensors *Proc. SPIE* **7292** 72921H
- [205] Chen Y J, Sun J, Liu Y J and Leng J S 2012 Variable stiffness property study on shape memory polymer composite tube *Smart Mater. Struct.* **21** 094021
- [206] Chen S B, Chen Y J, Feng N, Liu Y J and Leng J S, Experiment and analysis of morphing skin embedded with shape memory polymer composite tube *J. Intell. Mater. Syst. Struct.* under review
- [207] Gomez J C and Garcia E 2011 Morphing unmanned aerial vehicles *Smart Mater. Struct.* **20** 103001
- [208] Schonberg W P, Schafer F and Putzar R 2009 Some comments on the protection of lunar habitat against damage meteoroid impacts *J. Aerosp. Eng.* **23** 90–7
- [209] Hinkle J, Lin J and Kling D 2011 Design and materials study of secondary structures in deployable planetary and space habitats *52nd AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Denver, CO, April)* p 95047
- [210] www.crgrp.com/technology/portfolio/self-constructing-structures.html
- [211] Mallick K, Tupper M L, Arritt C B J and Paul C L 2003 Thermo-micromechanics of microcracking in a cryogenic pressure vessel *44th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Norfolk, VA, April)* vol 5, pp 3320–9
- [212] Mallick K, John C, Steven A, Tupper M L, Grimes-ledesma L, Lewis J C, Paul C and Welsh J S 2004 Ultralight linerless composite tanks for in-space application *AIAA Space 2004 Conf. and Exposition (San Diego, CA, Sept.)* vol 1, pp 1–13
- [213] Mallick K, John C, Ryan K, Steven A, Naseem M, Paul C and Welsh J S 2005 An integrated systematic approach to linerless composite tank development *46th AIAA/ASME/ASCE/AHS/ASC Structures, Structural Dynamics, and Materials Conf. (Austin, TX, April)* vol 5, pp 3553–69
- [214] Everhart M C, Stahl J, Traxler E and Havens E 2004 Shape memory polymer configurative tooling *Proc. SPIE* **5388** 87–94
- [215] Everhart M C and Stahl J 2005 Reusable shape memory polymer mandrels *Proc. SPIE* **5762** 27–34
- [216] www.crgrp.com/technology/overviews/mandrels.html
- [217] Zhang L 2012 *The Design and Research of a Smart Mandrel Based on Shape Memory Polymers* (Harbin: Harbin Institute of Technology)